

Effect of Processing Parameters and Microcontent Nb on the Microstructure and Properties of Medium Carbon Steels

G. R. Ebrahimi* and H. Arabshahi**

* *Metallurgy and Materials Engineering Department, Sabzevar Tarbiat Moallem University, Sabzevar, Iran*

** *Physics Department, Ferdowsi University of Mashhad, Mashhad, Iran*

e-mail: arabshahi@um.ac.ir

Submitted: 15/09/2010

Accepted: 20/11/2010

Appeared: 30/11/2010

©HyperSciences.Publisher

Abstract— Niobium-microalloyed steel has become a standard material in plate and strip for line pipe, automotive and construction use. The effects of controlled rolling parameters and microcontent Nb on the mechanical properties of medium carbon steels were studied in this work. For these purpose two steel grades, with and without niobium, was planed and after steelmaking and continuous casting, rolling process was done. Then, laboratory investigations such as microstructure, mechanical properties and grain size analysis were performed. Tensile and Charpy impact tests specimens were machined out of the central part of the rolled billets. The microstructure of the specimens was examined for each experimental condition using optical microscopy. The results indicate that, increasing the reheating temperature above the dissolution temperature of (Nb)(C, N) improved the impact energy values. By increasing the cooling rate from 0.5 to 1.5°C/s both tensile strength and impact toughness were improved. High elongation percent was also observed on samples reheated at higher temperature and/or cooled with the higher cooling rates. The obtained mechanical properties were related to the characteristics of microstructural components including acicular ferrite, retained austenite, pearlite and ferrite.

Keywords: Microalloyed Steel, Hot Rolling, Niobium, Microstructure, Mechanical Properties.

1. INTRODUCTION

Microalloyed steels due to high surface quality combined with low production cost, by removing heat treatment step after rolling, and environmental considerations are suitable alternatives for quench-tempered steels. These steels experience completely-controlled cooling after rolling or forging process. However components made of microalloyed steels have always suffered from lower toughness values compared to their quenched and tempered counter parts. This has limited their applications particularly for safety components where both high strength and toughness properties are required (Matlock D K 2005; Kundu A 2010). The first generation of microalloyed steels (C–Mn–V steels) had ferrite–pearlite microstructures and the low toughness values were associated to the inherent cleavage fracture mode of pearlite. Therefore researches have been focused on eliminating or minimizing the amount of pearlite that can be formed during post cooling. In recent years, the trend has been to modify the ferrite–pearlite microstructure with high impact toughness microstructures such as acicular ferrite

through a judicious control of thermomechanical processing parameters (Kundu A 2010; Wang LJ 2008; Yu Q 2004). Typically, niobium has a threefold influence on the mechanical properties of steel: 1) grain size refinement during hot forming, 2) precipitation hardening and 3) lowering the γ to α transition temperature (Ar3). Grain refinement is the only mechanism that simultaneously increases strength, toughness and ductility. This effect makes Nb the most effective microalloying element, even if added in small quantities. Nb(C, N) precipitates that have formed and grown at high temperature and in austenite phase prevent from grain coarsening in the subsequent stage of hot deformation. Other diffusion controlled process, that occur with solution of niobium in austenite, are retarding of γ to α transformation that cause to increase nucleation of ferrite and reduce grain growth rate, forming of quasi-equivalence structures like bainite and finally appearance very fine Nb(C, N) precipitates during transformation that being coherent interface cause to increase strength with precipitation hardening mechanism (Klinkenberg C 2006; Medina S F 1999; Abad R 2001). In the present article the influence of thermomechanical process parameters (reheating temperature, cooling rate) and chemical composition on the microstructural and mechanical properties was investigated.

* This work is supported by the Sabzevar Tarbiat Moallem University through contract with vice president of research and technology.

2. EXPERIMENTAL EQUIPMENT, MATERIAL AND PROCEDURE

The material used in this investigation was produced in an electric arc furnace equipped with semi-automatic charging system. Secondary steelmaking operations were performed in a ladle furnace with vacuum degassing units to eliminate oxygen as well as inclusion modification capabilities. For improving mechanical properties of primary steel, quantitative amount of niobium would be added to general composition of these steel. For this purpose after preparation melting of base composition in an electric arc furnace, in steel making process two grades (1, 2-3) of these steels with and without niobium provided, as shown in table (1), and then in continuous casting process, blooms produced with cross section 230*250mm². Then in heavy section mill the blooms were hot rolled to 125*125mm² billets. Finally in light section mill the billets hot rolled to 65 mm diameter bars out of which the specimens used in this investigation were machined out. Steel bars were inspected by magnetic particles inspection method to identify and remove any possible surface cracks.

Table 1. Chemical composition of steel investigated (wt %).

Designation	C	Si	Mn	S	Nb	N
1	0.36	0.42	1.08	0.01	-	130
2	0.30	0.39	0.98	0.006	0.036	220
3	0.30	0.39	0.97	0.015	0.041	145

To reveal prior austenite grain boundaries and to determine the effect of reheating temperature on austenite grain size, specimens with 15 mm diameter and 25 mm height with their axis parallel to the axis of the bar were prepared from the as received material. They were then heated in an electrical furnace with SiC heating elements between 1000 to 1300°C for 25 min followed by water quenching. The specimens were then tempered at 450°C for 4 h to improve grain boundary etching. After usual grinding and polishing operations they were etched in saturated aqueous solution of picric acid with addition of CuCl₂ at 70°C. Digital pictures were prepared by using optical microscopy and average austenite grain sizes were measured using the linear intercept method according to ASTM E112 standard.

The dissolution temperature of Nb carbonitrides was estimated using the following relationships proposed by Tamura (1), Prasad (2) and Adamczyk (3) whose steel compositions are the closest to the one used in this work (Tamura M 2001; Prasad S N 2003; Adamczyk J 2004).

$$\text{Log}[\text{Nb}][\text{C}] = -(6661/\text{T}) + 2.54 \quad (1)$$

$$\text{Log}(\text{Nb})(\text{C})^{0.83}(\text{N})^{0.14} = -(9800/\text{T}) + 4.46 \quad (2)$$

$$\text{Log}[\text{Nb}][\text{C}] = -(7290/\text{T}) + 3.04 \quad (3)$$

The above relationships lead to dissolution temperatures between 1185°C to 1225°C for both of microalloyed compositions. The billets were reheated to 1180°C or 1240°C in a continuous walking beam furnace for 60 min. The

selection of the reheating temperature was made with the objective to study the effect of smaller austenite grain size and larger carbonitrides (reheating at 1180°C) versus large austenite grain sizes and very fine carbonitrides (upon cooling from 1240°C) on final mechanical properties. Special pyrometer was used to measure the temperature of the billets at the exit of the walking beam furnace. The specimens were then immediately started to deform as shown schematically in Fig. 1. After 17 passed rolling and 93% reduction of area, the bars with 65mm diameter were produced. The as rolled bars were then cooled to room temperature with different cooling rates. These were approximately air cooled (0.5°C/s), and water-spray with forced air cooled (1.5°C/s). Tensile and impact test specimens were prepared from the centre of the deformed bars according to ASTM E8 and E23 standards, respectively. Metallography samples, perpendicular to the rolling direction, were extracted from the extremities of the impact test specimens. They were then cold mounted in bakelite, polished, and etched with 5% natal. An optical microscope instrumented by image analysis software was used for microstructure examination.

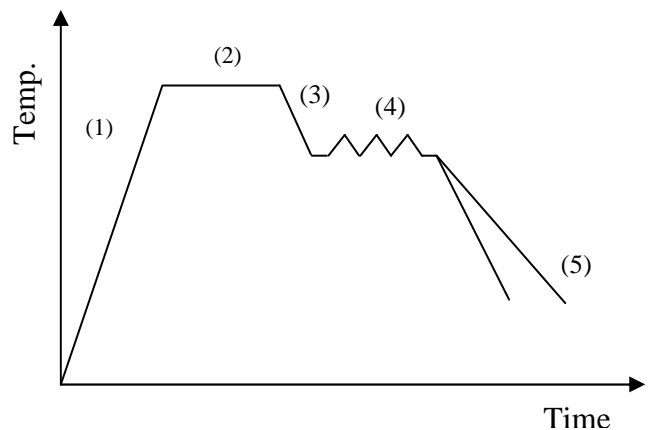


Fig. 1. Schematic diagram of thermomechanical processing: (1) Reheated to (1180,1250 °C) at a rate of 10 K/s; (2) Held for 20 min in reheating temperature; (3) gap time to receiving billets from furnace to mill; (4) Deformed at temperatures generally between (1150- 980 °C) (5) cooling after rolling process (0.5, 1.5 °C/s).

3. RESULTS AND DISCUSSION

Figures 2 and 3 show the variation of Charpy impact energy and elongation percent with chemical composition, cooling rate and reheating temperatures. The results indicate that, impact energy increases with increasing cooling rate, reheating temperature and with modification of chemical composition. As indicated in Fig. 2 impact energy increases from 73 to 85 J when cooling rate increases from 0.5 to 1.5°C/s for billets with 0.041 Nb reheated at 1240°C. It is interesting to note that, for the latter sample, i.e. sample with cooling rate (1.5°C/s) and 0.041 Nb, the elongation percent during tensile testing approaches 24.5%, which represents very good ductility. However the specimen without Nb and high content of C shows different behavior.

Figures 2 and 3 show the variation of Charpy impact energy and elongation percent with chemical composition, cooling rate and reheating temperatures. The results indicate that, impact energy increases with increasing cooling rate, reheating temperature and with modification of chemical composition. As indicated in figure 2 impact energy increases from 73 to 85 J when cooling rate increases from 0.5 to 1.5 °C/s for billets with 0.041 Nb reheated at 1240 °C. It is interesting to note that, for the latter cooling condition (i.e. 1.5°C/s) the elongation percent during tensile testing approaches 24.5%, which represents very good ductility. However the specimen without Nb and high content of C shows different behaviour.

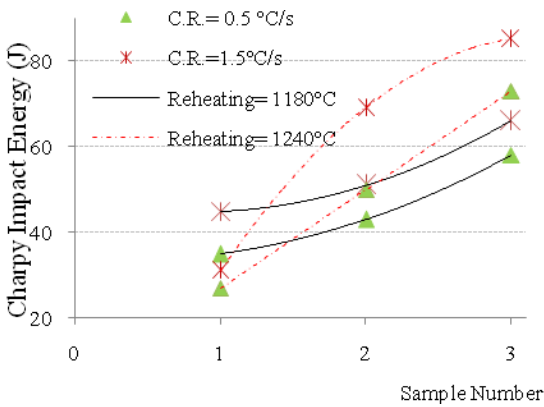


Fig. 2. Variation of Charpy impact energy with rolling parameters.

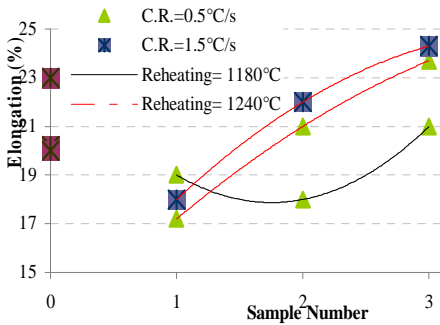


Fig. 3. Variation of elongation with rolling parameters.

The influence of thermomechanical processing parameters on yield and tensile strengths are illustrated in Figs.4 and 5. The results indicate that, yield strength decreases with increasing cooling rate for both reheating temperatures while increasing cooling rate and reheating temperature results to higher tensile strength values.

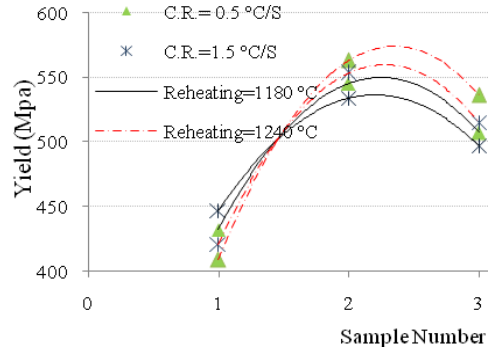


Fig 4 Variation of yield strength with Rolling Parameters.

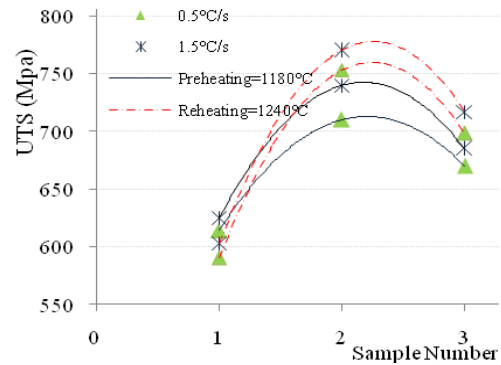


Fig.5. Variation of tensile strength with Rolling Parameters.

Figure 6 and 7 show the variation of mean austenite grain size with reheating temperature. As indicated, for reheating temperatures between 1000 and 1150°C the average austenite grain size increases slightly, passing from 47µm at 1000°C to 80 µm at 1150°C. However, a sudden increase is observed after 1200°C, which becomes even more important at 1250°C where the average grain size reaches 145µm. This clearly indicates that, the lower end dissolution temperature of (Nb) (C, N) precipitates is in the vicinity of 1200°C. The obtained results confirm that, the dissolution temperature of (Nb) (C, N) precipitates is in the interval 1200–1220°C as predicted based on relations reported previously.

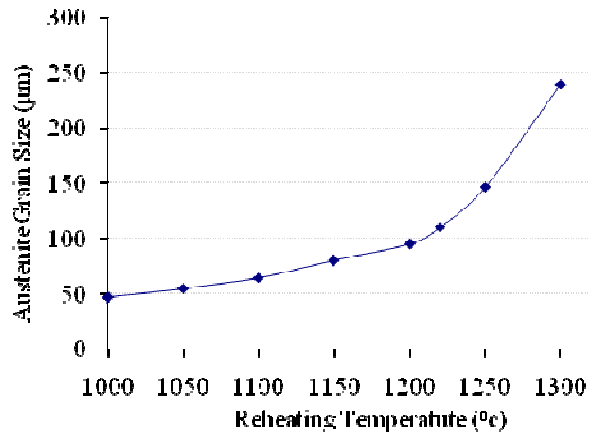


Fig 6. Variations of austenite grain size versus reheating temperature.

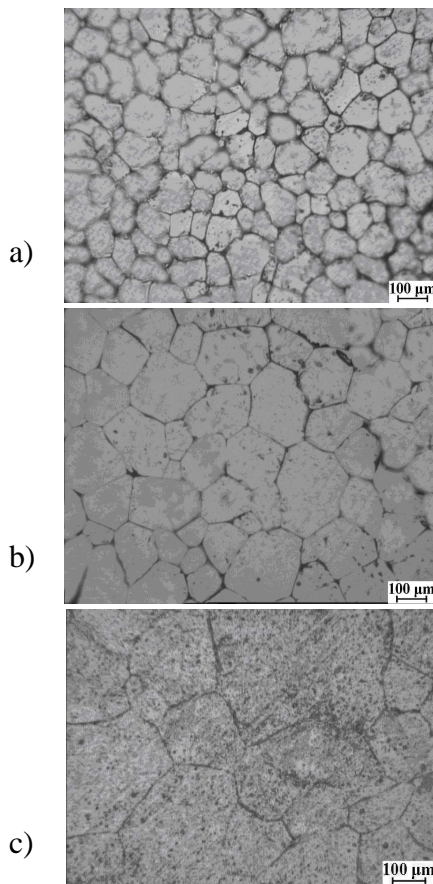


Fig 7. Optical micrography of austenite grain size in different reheating temperature.

The influence of rolling parameters on the propensity of the microstructure to produce semi-equilibrium phases is illustrated in Figs. 8(a-f). For instance, the microstructure of the second sample reheated at 1180°C and 0.5°C/s cooling rate is composed of polygonal ferrite, pearlite and quantitative acicular ferrite (Fig. 8(c)) but by increasing the reheating temperature to 1240°C the volume percent of pearlite and granular ferrite decreases and acicular ferrite increased (Fig. 8(d)). Increasing the cooling rate to 1.5°C/s eliminates almost all the pearlite and granular ferrite and replaces them by acicular ferrite as can be observed in Figs. 8(f).

At the higher reheating temperature, the increase in the amount of acicular ferrite (Fig. 8f) can be related to significantly higher austenite grain sizes of the specimen. Reheating at 1180°C and 1240°C produces mean austenite grain sizes of 85 and 145μm, respectively. With respect to transformation, austenite grain boundaries are preferred sites for the nucleation of proeutectoid ferrite, pearlite and bainite. Consequently, with larger austenite grains, fewer nucleation sites will be available for the above phases and the diffusion controlled transformation process becomes limited. As a result, upon transformation, intragranular nucleation will be promoted in expense of grain boundary transformation products. It is well known that, acicular ferrite nucleates on inclusions located at the interior of austenite grains, by a combination of displacive and reconstructive mechanisms

with less need to diffusion than products, such as ferrite and pearlite, that are diffusion controlled (Wang YW 2010; Shanmugam S 2007; Bhadeshia H. K. D. H 1999). Finally, by initially increasing austenite grain size, the nucleation of acicular ferrite is promoted and the amount of pearlite is reduced as can be observed by comparing Figs. 8(c), 8(d) and 8(e), 8(f).

Increasing cooling rate, decreases the diffusion time and reduces the transformation temperature, thus limiting the effectiveness of reconstructive mechanisms. Also, transformation at lower temperatures enhances displacive mechanisms and therefore promotes shear transformation products such as acicular ferrite (Bhadeshia H. K. D. H 1999; Lourenco N.J 2001; Bhadeshia H. K. D. H 2006).

As reported in Fig. 2, Charpy impact energy increases with increasing cooling rate and reheating temperature. This can be attributed to the volume percent of pearlite and acicular ferrite as well as to the size of (Nb) (C, N) particles. Acicular ferrite has a chaotic type structure and its multidirectional thin plates deflect crack propagation whereas pearlite is susceptible to cleavage fracture. Thus, increasing acicular ferrite and decreasing pearlite, improves significantly impact toughness values. Specifically, increased acicular ferrite content obtained at higher cooling rates and reheating temperature should improve Charpy impact energy (Bhadeshia H.K.D.H 1999; Bhadeshia H. K. D. H 2006; Fuentes M. D 2003; Matlock D.K 2001; Babakhani A 2010).

Acicular ferrite is usually accompanied with some retained austenite. So, the microstructures of the specimens in Figs. 8(d-f) consisted of acicular ferrite with significant volume percent of retained austenite. The latter transforms to martensite during deformation, so increase plastic deformation and result to higher percent elongation. The decrease in yield strength with increasing cooling rate, as observed in Fig. 4, can be related to the lower content of pearlite, presence of low strength ferrite, and some austenite in agreement with results reported by other investigators. Also, the higher yield strength of specimens with 1240°C reheating temperature compared to those reheated at 1180°C can be related to the precipitation of NbC dissolved during reheating at 1240°C, which does not exist at the lower reheating temperature. By contrast, the higher yield strength obtained for specimens without Nb, reheated at 1180°C and cooled with 0.5°C/s can be attributed to the presence of a higher volume percent of pearlite. Therefore, in samples without Nb where the microstructure consists mainly of pearlite, this constituent determines the yield strength; whereas, in samples consisting Nb, precipitates have the major role in determining the yield strength. The increase in tensile strength with cooling rate observed for both reheating temperatures (Fig. 5), may be related to the transformation of retained austenite (presents in acicular ferrite) to martensite during uniform straining. The higher resistance of martensite to deformation increases strain hardening and ultimately the tensile strength (DeArdo AJ 2009; Altuna MA 2009; Lopez B 2008; Topcu O 2009; Jorge-Badiola D 2010).

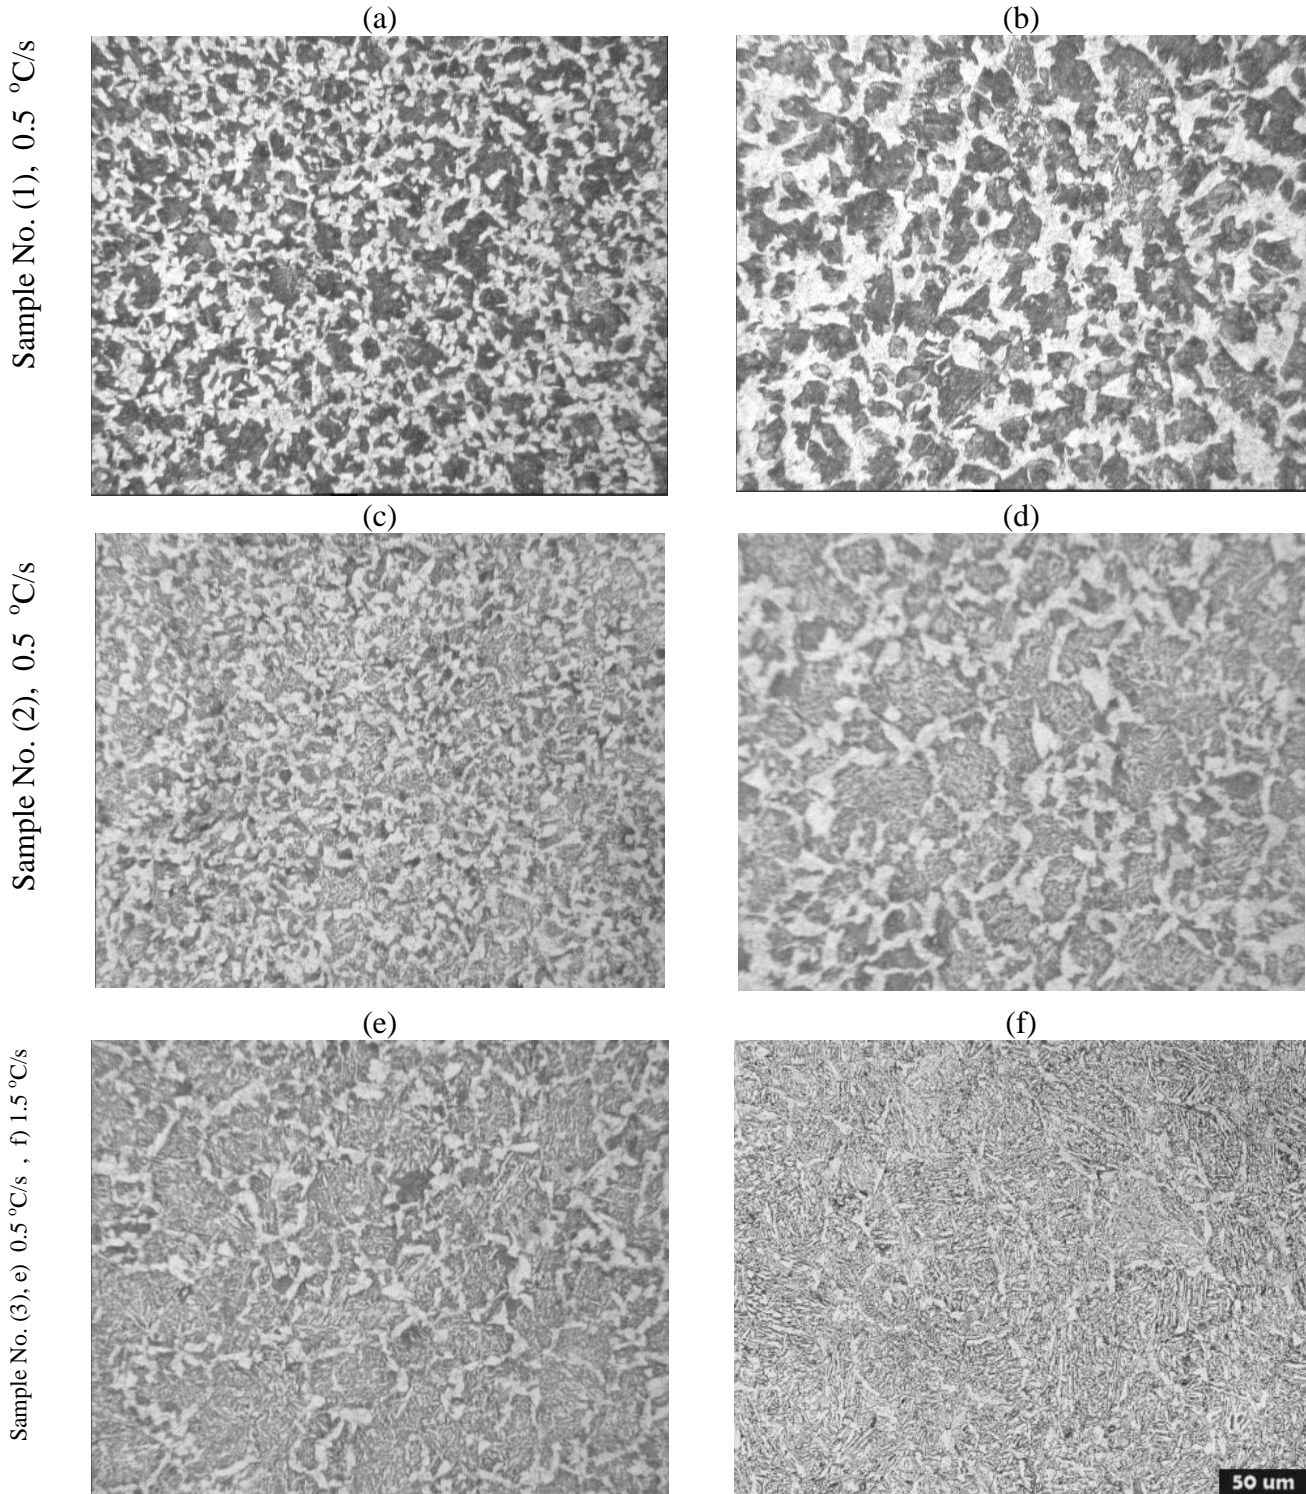


Fig 8. Showing Optical Micrography of Various Samples: (a,b): Sample Number (1,2), (c, d): Sample Number 2 (e, f): Sample Number 3. Cooling Rate in all Micrographs was 0.5°C/s (except f that was 1.5°C/s)

4. CONCLUSION

- Hot rolling processing parameters to obtain high strength-high impact toughness Nb microalloyed steels were optimized.

- Increasing reheating temperature from 1180 to 1240°C decreased considerably pearlite content in samples

consisting Nb, while the volume percent of acicular ferrite increased. The high volume fraction of acicular ferrite as well as the presence of very fine Nb(C, N) precipitates

increases the impact toughness and tensile strength simultaneously.

- Increasing cooling rate decreases pearlite content and increases acicular ferrite volume percent. Increasing cooling rate up to 1.5°C/s produces acicular ferrite in expense of pearlite and granular ferrite. These microstructural variations increase impact energy, tensile strength, and elongation percent of specimens with 1240°C reheating temperature.

ACKNOWLEDGMENTS

A grant from Tarbiat Moallem University of Sabzevar is gratefully acknowledged.

REFERENCES

- Abad R., Fernandez A.I., Lopez B., J.M.Rodriguez-Ibabe, (2001) Interaction between Recrystallization and Precipitation during Multipass Rolling in a Low Carbon Niobium Microalloyed Steel, *ISIJ International*, Vol. 41, No. 11, pp. 1373–1382.
- Adamczyk J., (2004) *Engineering of Metallic Materials*, The Silesian University of Technology Publishers, Gliwice, (in Polish).
- Altuna MA, Iza-Mendia A, Gutierrez I, (2009) Precipitation Strengthening Produced By The Formation In Ferrite Of Nb Carbides, *Metallurgia Italiana* Issue: 6 Pages: 41-47.
- Babakhani, A; Ziaei, SMR; Kiani-Rashid, AR, (2010) Investigation on the effects of hot forging parameters on the austenite grain size of vanadium microalloyed forging steel (30MSV6), *Journal Of Alloys And Compounds* Vols: 490 Issue: 1-2 pp. 572-575.
- Bhadeshia H.K.D.H., (1999) The bainite transformation: *Materials Science and Engineering A* 273–275 58–66.
- DeArdo, AJ; Hua, MJ; Cho, KG, et al. (2009) On strength of microalloyed steels: an interpretive review, *Materials Science And Technology* Vols: 25 Issue: 9 pp. 1074-1082.
- Fuentes M. D., Gutiérrez I., (2003) Analysis of different acicular ferrite microstructures generated in a medium-carbon molybdenum steel, *Materials Science and Engineering A* 363 316–324.
- Jorge-Badiola, D; Iza-Mendia, A; Rodriguez-Ibabe, JM, et al. (2010) Influence of Thermomechanical Processing on the Austenite-Pearlite Transformation in High Carbon Vanadium Microalloyed Steels, *Isij International*, vols. 50:: 4: P. 546-555.
- Klinkenberg C., Jansto S.G., (2006) Niobium Microalloyed Steels for Long Products, *International Conference on New Development in Ferrous and Forged Products*, TMS, Winter Park, CO.
- Kundu A, Davis CL, Strangwood M, (2010) Grain Structure Development during Reheating and Deformation of Niobium-Microalloyed Steels, *Materials And Manufacturing Processes*, Vols. 25; pp. 125-132.
- Lopez B, Rodriguez-Ibabe JM. (2008) Thermomechanical Process Variables Affecting Austenite Microstructure Homogeneity In Microalloyed Steels, *New Developments On Metallurgy And Applications Of High Strength Steels*:
- Lourenco N.J., Jorge A.M. Jr, Rollo J.M.A., Balancin O., (2001) Plastic Behavior of Medium Carbon Vanadium Microalloyed Steel at Temperatures Near $\gamma \leftrightarrow \alpha$ Transformation, *Materials Research*, Vol. 4, No. 3, 149-156.
- Matlock D.K., Krauss G., Speer J.G., (2005) New Microalloyed Steel Application for the Automotive Sector, *Materials Science Forum*, Vols. 500-501 pp.87-96.
- Matlock D.K., Krauss G., Speer J.G., (2001) Microstructure and properties of direct-cooled microalloy forging steels, *Journal of materials processing technology* 117 324- 328.
- Medina S.F., Quispe A., Valles P., Banos J.L., (1999) Recrystallization- Precipitation Interaction Study of Two Carbon Niobium Microalloyed Steels, *ISIJ International*, Vol. 39, No. 9, pp. 913-922.
- Prasad S.N., Mediratta S.R., D.S. Sarma, (2003) Influence of austenitisation temperature on the structure and properties of weather resistant steels, *Materials Science and Engineering A* 358 288_297.
- Shanmugam S., Ramiseti N.K., Misra R.D.K., Mannering T., Panda D., Jansto S., (2007) Effect of cooling rate on the microstructure and mechanical properties of Nb-microalloyed steels, *Materials Science and Engineering A* 460–461 335–343.
- Tamura M., Ikeda K., Esaka H. And Shinozuka K., (2001) Precipitation Behavior of NbC in 9%Cr1%Mo0.2%VNb Steel, *ISIJ International*, Vol. 41, No. 8, pp. 908–914.
- Topcu O., Ubeyli M., (2009) on the microstructural and mechanical characterizations of a low carbon and microalloyed steel, *Materials and Design* 30 3274–3278.
- Wang LJ, Yao LD, Ren HP, (2008) Study on deformation induced ferrite transformation in mild steels with or without niobium , *Physical And Numerical Simulation Of Materials Processing*, Vols. 575-578: pp. 898-903.
- Wang YW, Feng C, Xu FY, et al. (2010) Influence of Nb on Microstructure and Property of Low-Carbon Mn-Series Air-Cooled Bainitic Steel, *Journal Of Iron And Steel Research International* Vols: 17 Issue: pp.: 49-53.
- Yu Q., Wang Z., X.Liu, Wang G., (2004) Effect of microcontent Nb in solution on the strength of low carbon steels, *Materials Science and Engineering A* 379 384–390.