

Provided for non-commercial research and education use.
Not for reproduction, distribution or commercial use.



(This is a sample cover image for this issue. The actual cover is not yet available at this time.)

This article appeared in a journal published by Elsevier. The attached copy is furnished to the author for internal non-commercial research and education use, including for instruction at the authors institution and sharing with colleagues.

Other uses, including reproduction and distribution, or selling or licensing copies, or posting to personal, institutional or third party websites are prohibited.

In most cases authors are permitted to post their version of the article (e.g. in Word or Tex form) to their personal website or institutional repository. Authors requiring further information regarding Elsevier's archiving and manuscript policies are encouraged to visit:

<http://www.elsevier.com/copyright>



Contents lists available at SciVerse ScienceDirect

Applied Catalysis B: Environmental

journal homepage: www.elsevier.com/locate/apcatb

Review

A review on the visible light active titanium dioxide photocatalysts for environmental applications[☆]

Miguel Pelaez^a, Nicholas T. Nolan^b, Suresh C. Pillai^b, Michael K. Seery^c, Polycarpos Falaras^d, Athanassios G. Kontos^d, Patrick S.M. Dunlop^e, Jeremy W.J. Hamilton^e, J. Anthony Byrne^e, Kevin O'Shea^f, Mohammad H. Entezari^g, Dionysios D. Dionysiou^{a,*}

^a Environmental Engineering and Science Program, School of Energy, Environmental, Biological, and Medical Engineering, University of Cincinnati, Cincinnati, OH 45221-0012, USA

^b Center for Research in Engineering Surface Technology (CREST), FOCAS Institute, Dublin Institute of Technology, Kevin St, Dublin 8, Ireland

^c School of Chemical and Pharmaceutical Sciences, Dublin Institute of Technology, Kevin St., Dublin 8, Ireland

^d Institute of Physical Chemistry, NCSR Demokritos, 15310 Aghia Paraskevi, Attiki, Greece

^e Nanotechnology and Integrated BioEngineering Centre, School of Engineering, University of Ulster, Northern Ireland, BT37 0QB, United Kingdom

^f Department of Chemistry and Biochemistry, Florida International University, University Park, Miami, FL 3319, USA

^g Department of Chemistry, Ferdowsi University of Mashhad, Mashhad 91775, Iran

ARTICLE INFO

Article history:

Received 28 March 2012

Received in revised form 21 May 2012

Accepted 25 May 2012

Available online xxx

Keywords:

TiO₂
Visible
Solar
Water
Treatment
Air purification
Disinfection
Non-metal doping
Anatase
Rutile
N-TiO₂
Metal doping
Environmental application
Reactive oxygen species
Photocatalysis
Photocatalytic
EDCs
Cyanotoxins
Emerging pollutants

ABSTRACT

Fujishima and Honda (1972) demonstrated the potential of titanium dioxide (TiO₂) semiconductor materials to split water into hydrogen and oxygen in a photo-electrochemical cell. Their work triggered the development of semiconductor photocatalysis for a wide range of environmental and energy applications. One of the most significant scientific and commercial advances to date has been the development of visible light active (VLA) TiO₂ photocatalytic materials. In this review, a background on TiO₂ structure, properties and electronic properties in photocatalysis is presented. The development of different strategies to modify TiO₂ for the utilization of visible light, including non metal and/or metal doping, dye sensitization and coupling semiconductors are discussed. Emphasis is given to the origin of visible light absorption and the reactive oxygen species generated, deduced by physicochemical and photo-electrochemical methods. Various applications of VLA TiO₂, in terms of environmental remediation and in particular water treatment, disinfection and air purification, are illustrated. Comprehensive studies on the photocatalytic degradation of contaminants of emerging concern, including endocrine disrupting compounds, pharmaceuticals, pesticides, cyanotoxins and volatile organic compounds, with VLA TiO₂ are discussed and compared to conventional UV-activated TiO₂ nanomaterials. Recent advances in bacterial disinfection using VLA TiO₂ are also reviewed. Issues concerning test protocols for real visible light activity and photocatalytic efficiencies with different light sources have been highlighted.

© 2012 Elsevier B.V. All rights reserved.

Contents

1. Titanium dioxide – an introduction	332
1.1. TiO ₂ structures and properties	332
1.2. Electronic processes in TiO ₂ photocatalysis	332
1.3. Recombination	333
1.4. Strategies for improving TiO ₂ photoactivity	334

[☆] All authors have contributed equally to this review.

* Corresponding author. Tel.: +1 513 556 0724; fax: +1 513 556 2599.

E-mail address: dionysios.d.dionysiou@uc.edu (D.D. Dionysiou).

0926-3373/\$ – see front matter © 2012 Elsevier B.V. All rights reserved.

<http://dx.doi.org/10.1016/j.apcatb.2012.05.036>

2.	Development of visible light active (VLA) titania photocatalysts	334
2.1.	Non metal doping	334
2.1.1.	Nitrogen doping	334
2.1.2.	Other non-metal doping (F, C, S)	336
2.1.3.	Non-metal co-doping	336
2.1.4.	Oxygen rich TiO ₂ modification	336
2.2.	Metal deposition	336
2.2.1.	Noble metal and transition metal deposition	336
2.3.	Dye sensitization in photocatalysis	337
2.4.	Coupled semiconductors	337
2.5.	Defect induced VLA photocatalysis	339
3.	Oxidation chemistry, the reactive oxygen species generated and their subsequent reaction pathways	339
3.1.	Reactive oxygen species and reaction pathways in VLA TiO ₂ photocatalysis	339
3.2.	Photoelectrochemical methods for determining visible light activity	340
4.	Environmental applications of VLA TiO ₂	342
4.1.	Water treatment and air purification with VLA photocatalysis	342
4.2.	Water disinfection with VLA photocatalysis	343
5.	Assessment of VLA photocatalyst materials	344
5.1.	Standardization of test methods	344
5.2.	Challenges in commercializing VLA photocatalysts	346
6.	Conclusions	346
	Acknowledgments	346
	References	346

1. Titanium dioxide – an introduction

1.1. TiO₂ structures and properties

Titanium dioxide (TiO₂) exists as three different polymorphs; anatase, rutile and brookite [1]. The primary source and the most stable form of TiO₂ is rutile. All three polymorphs can be readily synthesised in the laboratory and typically the metastable anatase and brookite will transform to the thermodynamically stable rutile upon calcination at temperatures exceeding ~600 °C [2]. In all three forms, titanium (Ti⁴⁺) atoms are co-ordinated to six oxygen (O²⁻) atoms, forming TiO₆ octahedra [3]. Anatase is made up of corner (vertice) sharing octahedra which form (001) planes (Fig. 1a) resulting in a tetragonal structure. In rutile the octahedra share edges at (001) planes to give a tetragonal structure (Fig. 1b), and in brookite both edges and corners are shared to give an orthorhombic structure (Fig. 1c) [2,4–7].

Titanium dioxide is typically an *n*-type semiconductor due to oxygen deficiency [8]. The band gap is 3.2 eV for anatase, 3.0 eV for rutile, and ~3.2 eV for brookite [9–11]. Anatase and rutile are the main polymorphs and their key properties are summarized in Table 1 [12,5,13]. TiO₂ is the most widely investigated photocatalyst due to high photo-activity, low cost, low toxicity and good chemical and thermal stability [12,14,15]. In the past few decades there have been several exciting breakthroughs with respect to titanium dioxide. The first major advance was in 1972 when Fujishima and Honda reported the photoelectrochemical splitting of water using a TiO₂ anode and a Pt counter electrode [16]. Titanium dioxide photocatalysis was first used for the remediation of environmental pollutants in 1977 when Frank and Bard reported the reduction of CN⁻ in water [17,18]. This led to a dramatic increase in the research in this area because of the potential for water and air purification through utilization of “free” solar energy [12,13,19]. Other significant breakthroughs included Wang et al. (1997), who reported TiO₂ surfaces with excellent anti-fogging and self-cleaning abilities, attributed to the super hydrophilic properties of the photoexcited TiO₂ surfaces [20] and use of nano titanium dioxide in an efficient dye sensitized solar cell (DSSC), reported by Graetzel and O'Regan in 1991 [21].

1.2. Electronic processes in TiO₂ photocatalysis

Photocatalysis is widely used to describe the process in which the acceleration of a reaction occurs when a material, usually a

semiconductor, interacts with light of sufficient energy (or of a certain wavelength) to produce reactive oxidizing species (ROS) which can lead to the photocatalytic transformation of a pollutant. It must be noted that during the photocatalytic reaction, at least two events must occur simultaneously in order for the successful production of reactive oxidizing species to occur. Typically, the first involves the oxidation of dissociatively adsorbed H₂O by photogenerated holes, the second involves reduction of an electron acceptor (typically dissolved oxygen) by photoexcited electrons; these reactions lead to the production of a hydroxyl and superoxide radical anion, respectively [22].

It is clear that photocatalysis implies photon-assisted generation of catalytically active species rather than the action of light as a catalyst in a reaction [23,24]. If the initial photoexcitation process occurs in an adsorbate molecule, which then interacts with the ground state of the catalyst substrate, the process is referred to as a “catalyzed photoreaction”, if, on the other hand, the initial photoexcitation takes place in the catalyst substrate and the photoexcited catalyst then interacts with the ground state adsorbate molecule, the process is a “sensitized photoreaction”. In most cases, heterogeneous photocatalysis refers to semiconductor photocatalysis or semiconductor-sensitized photoreactions [22].

In photocatalysis, light of energy greater than the band gap of the semiconductor, excites an electron from the valence band to the conduction band (see Fig. 2). In the case of anatase TiO₂, the band gap is 3.2 eV, therefore UV light ($\lambda \leq 387$ nm) is required. The absorption of a photon excites an electron to the conduction band (e_{CB}⁻) generating a positive hole in the valence band (h_{VB}⁺) (Eq. (1.1)).



Charge carriers can be trapped as Ti³⁺ and O⁻ defect sites in the TiO₂ lattice, or they can recombine, dissipating energy [25]. Alternatively, the charge carriers can migrate to the catalyst surface and initiate redox reactions with adsorbates [26]. Positive holes can oxidize OH⁻ or water at the surface to produce •OH radicals (Eq. (1.2)) which, are extremely powerful oxidants (Table 2). The hydroxyl radicals can subsequently oxidize organic species with mineralization producing mineral salts, CO₂ and H₂O (Eq. (1.5)) [27].






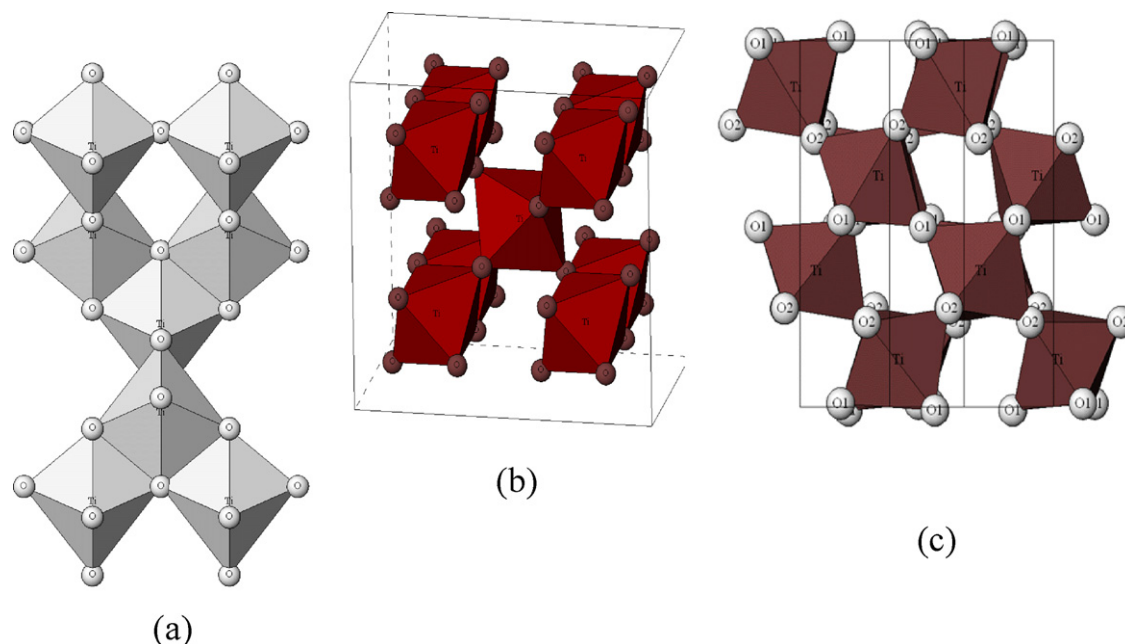


Fig. 1. Crystalline structures of titanium dioxide (a) anatase, (b) rutile, (c) brookite (Reprinted with permission from Katsuhiro Nomura (nomura-k@aist.go.jp; http://staff.aist.go.jp/nomura-k/english/itscgallery-e.htm) Copyright (2002)).



Electrons in the conduction band can be rapidly trapped by molecular oxygen adsorbed on the titania particle, which is reduced to form superoxide radical anion ($\text{O}_2^{\bullet -}$) (Eq. (1.4)) that may further react with H^+ to generate hydroperoxyl radical ($\bullet\text{OOH}$) (Eq. (1.6)) and further electrochemical reduction yields H_2O_2 (Eq. (1.7)) [28,29]. These reactive oxygen species may also contribute to the oxidative pathways such as the degradation of a pollutant (Eqs. (1.8) and (1.9)) [25,27,28].

1.3. Recombination

Recombination of photogenerated charge carriers is the major limitation in semiconductor photocatalysis as it reduces the overall quantum efficiency [29]. When recombination occurs, the

excited electron reverts to the valence band without reacting with adsorbed species (Eq. (1.2)) [30] non-radiatively or radiatively, dissipating the energy as light or heat [6,31].

Recombination may occur either on the surface or in the bulk and is in general facilitated by impurities, defects, or all factors which introduce bulk or surface imperfections into the crystal [29,32]. Serpone et al. found that trapping excited electrons as Ti^{3+} species occurred on a time scale of ~ 30 ps and that about 90% or more of the photogenerated electrons recombine within 10 ns

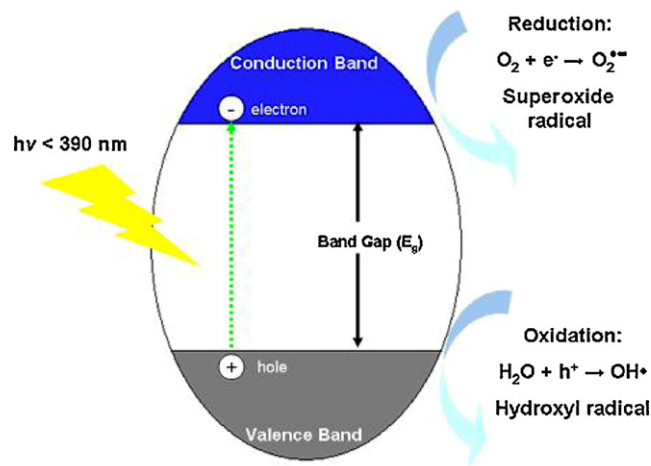


Fig. 2. Schematic of TiO_2 photocatalytic mechanism.

Table 1
Physical and structural properties of anatase and rutile TiO_2 .

Property	Anatase	Rutile
Molecular weight (g/mol)	79.88	79.88
Melting point ($^{\circ}\text{C}$)	1825	1825
Boiling point ($^{\circ}\text{C}$)	2500–3000	2500–3000
Light absorption (nm)	<390	<415
Mohr's Hardness	5.5	6.5–7.0
Refractive index	2.55	2.75
Dielectric constant	31	114
Crystal structure	Tetragonal	Tetragonal
Lattice constants (\AA)	$a = 3.78$ $c = 9.52$	$a = 4.59$ $c = 2.96$
Density (g/cm^3)	3.79	4.13
Ti–O bond length (\AA)	1.94 (4)	1.95 (4)
	1.97 (2)	1.98 (2)

Table 2
Standard electrochemical reduction potentials of common oxidants.

Oxidant	Half-cell reaction	Oxidation potential (V)
$\bullet\text{OH}$ (Hydroxyl radical)	$\bullet\text{OH} + \text{H}^+ + e^- \rightarrow \text{H}_2\text{O}$	2.80
O_3 (Ozone)	$\text{O}_3(\text{g}) + 2\text{H}^+ + 2e^- \rightarrow \text{O}_2(\text{g}) + \text{H}_2\text{O}$	2.07
H_2O_2 (Hydrogen peroxide)	$\text{H}_2\text{O}_2 + 2\text{H}^+ + 2e^- \rightarrow 2\text{H}_2\text{O}$	1.77
HClO (Hypochlorous acid)	$\text{Cl}_2(\text{g}) + 2e^- \rightarrow 2\text{Cl}^-$	1.49
Cl^- (Chlorine)	$2\text{HClO} + 2\text{H}^+ + 2e^- \rightarrow \text{Cl}_2 + 2\text{H}_2\text{O}$	1.36

[33]. Doping with ions [34–36], heterojunction coupling [37–39] and nanosized crystals [40,41] have all been reported to promote separation of the electron–hole pair, reducing recombination and therefore improve the photocatalytic activity. For example, the TiO₂ crystallites of Evonik (Degussa) P25 contain a combination of anatase (~80%) and rutile (~20%). The conduction band potential of rutile is more positive than that of anatase which means that the rutile phase may act as an electron sink for photogenerated electrons from the conduction band of the anatase phase. Many researchers attribute the high photocatalytic activity of this preparation to the intimate contact between two phases, enhancing separation of photogenerated electrons and holes, and resulting in reduced recombination [42].

1.4. Strategies for improving TiO₂ photoactivity

Various strategies have been adopted for improving the photocatalytic efficiency of TiO₂. They can be summarized as either morphological modifications, such as increasing surface area and porosity, or as chemical modifications, by incorporation of additional components in the TiO₂ structure. Although visible light active (VLA) TiO₂ photocatalysts require chemical modifications, which will be reviewed in the next section, their overall efficiencies have been significantly enhanced by controlling the semiconductor morphology.

The most commonly used TiO₂ morphology is that of monodispersed nanoparticles wherein the diameter is controlled to give benefits from the small crystallite size (high surface area, reduced bulk recombination) without the detrimental effects associated with very small particles (surface recombination, low crystallinity) [43]. One dimensional (1D) titania nanostructures (nanotubes, nanorods, nanowires, nanobelts, nanoneedles) have been also formed by hydrothermal synthesis but high emphasis was given in titania self-assembled nanotubular films grown by electrochemical anodization on titanium metal foils. Advantages of such structures is their tailored morphology, controlled porosity, vectorial charge transfer [44,45] and low recombination at grain boundaries that result in enhanced performance in photoinduced applications, mainly in photocatalysis [44,46,47]. An interesting use of TiO₂ nanotubes in photocatalytic applications is the growth of freestanding flow-through membranes [44].

2. Development of visible light active (VLA) titania photocatalysts

2.1. Non metal doping

2.1.1. Nitrogen doping

Ultraviolet light makes up only 4–5% of the solar spectrum, whereas approximately 40% of solar photons are in the visible region. A major drawback of pure TiO₂ is the large band gap meaning it can only be activated upon irradiation with photons of light in the UV domain ($\lambda \leq 387$ nm for anatase), limiting the practical efficiency for solar applications [48–50]. Therefore, in order to enhance the solar efficiency of TiO₂ under solar irradiation, it is necessary to modify the nanomaterial to facilitate visible light absorption. Non-metal doping of TiO₂ has shown great promise in achieving VLA photocatalysis, with nitrogen being the most promising dopant [51,52].

Nitrogen can be easily introduced in the TiO₂ structure, due to its comparable atomic size with oxygen, small ionization energy and high stability. It was in 1986 when Sato discovered that addition of NH₄OH in a titania sol, followed by calcination of the precipitated powder, resulted in a material that exhibited a visible light response [53,54]. Later on, Asahi and co-workers explored for first

time the visible light activity of N-doped TiO₂ produced by sputter deposition of TiO₂ under an N₂/Ar atmosphere, followed by annealing under N₂ [55]. Since then, there have been many reports dealing with nitrogen doping of TiO₂. Significant efforts are being devoted to investigating the structural, electronic and optical properties of N-doped TiO₂, understanding the underlying mechanisms and improving the photocatalytic and self-cleaning efficiency under visible and solar light [56–58]. Comprehensive reviews have been published which summarize representative results of these studies [59,60]. Model pollutants that have been reported to be effectively degraded by VLA photocatalyst include phenols, methylene blue, methyl orange (although dyes have strong absorption in the visible range) and rhodamine B, as well as several gaseous pollutants (e.g., volatile organic compounds, nitrogen oxides).

For the efficient incorporation of nitrogen into TiO₂ either in the bulk or as a surface dopant, both dry and wet preparation methods have been adopted. Physical techniques such as sputtering [61–65] and ion implantation [66,67], rely on the direct treatment of TiO₂ with energetic nitrogen ions. Gas phase reaction methods [68–70], atomic layer deposition [71] and pulsed laser deposition [72] have been successfully applied to prepare N–TiO₂, as well. However, the most versatile technique for the synthesis of N–TiO₂ nanoparticles is the sol–gel method, which requires relatively simple equipment and permits fine control of the material's nanostructure, morphology and porosity. Simultaneous TiO₂ growth and N doping is achieved by hydrolysis of titanium alkoxide precursors in the presence of nitrogen sources. Typical titanium salts (titanium tetrachloride) and alkoxide precursors (including titanium tetra-isopropoxide, tetrabutyl orthotitanate) have been used. Nitrogen containing precursors used include aliphatic amines, nitrates, ammonium salts, ammonia and urea [73–75]. The synthesis route involves several steps; however, the main characteristic is that precursor hydrolysis is usually performed at room temperature. The precipitate is then dried to remove solvents, pulverized and calcined at temperatures from 200 to 600 °C.

One promising way to increase the nitrogen content in the TiO₂ lattice is to combine the titanium precursors with a nitrogen-containing ligand, such as Ti⁴⁺-bipyridine or Ti⁴⁺-amine complexes [76,77]. An alternative soft chemical route is based on the addition of urea during the condensation of an alkoxide acidified solution, leading to interstitial surface doping and shift of the absorption edge well into the visible spectral range (from 3.2 to 2.3 eV) [78]. An innovative sol–gel related technique for the preparation of efficient visible-light active nanostructured TiO₂ is the templating sol–gel method, utilizing titanium precursors combined with nitrogen-containing surfactants. Specifically, successful synthesis of visible light activated N–TiO₂ has been achieved by a simple sol–gel method employing dodecylammonium chloride (DDAC) as surfactant [79]. The DDAC surfactant acts simultaneously as a pore templating material to tailor-design the structural properties of TiO₂ (see Fig. 3) as well as a nitrogen dopant to induce visible-light photoactivity and unique reactivity and functionality for environmental applications [80,81].

In a different approach N–TiO₂ was synthesized via two successive steps: synthesis of TiO₂ and then nitrogen doping using various nitrogen-containing chemicals (e.g. urea, ethylamine, NH₃ or gaseous nitrogen) at high temperatures [52,82–84] or inductively coupled plasma containing a wide range of nitrogen precursors [85]. In that case, the nitrogen atoms predominantly resided on the TiO₂ surface. The origin of the visible-light photocatalytic activity in these methods may arise from condensed aromatic s-triazine compounds containing melem and melon units [73].

Although most reports on N–TiO₂ concern the anatase polymorphic phase, visible light active N–TiO₂ with anatase-rutile mixed phase (Fig. 4) has also been prepared by tuning the parameters of

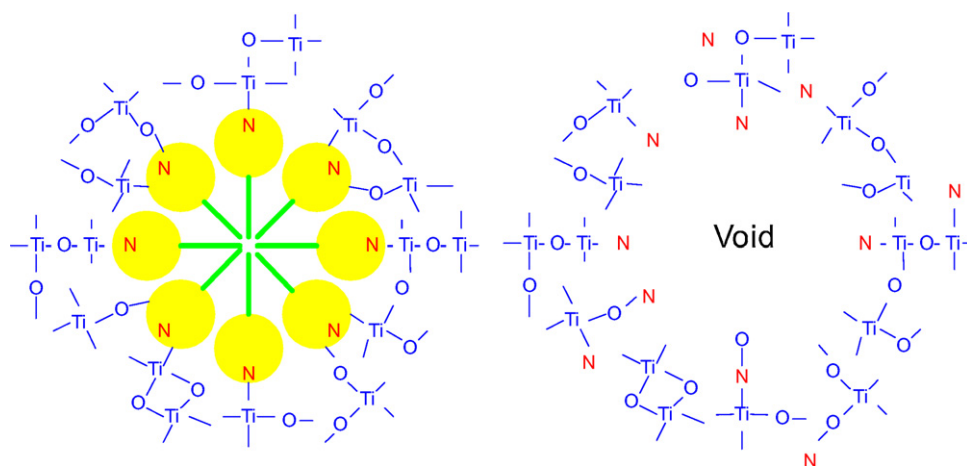


Fig. 3. Templating sol-gel method utilizing nitrogen containing surfactants as both nitrogen source and pore template material. (Reprinted with permission from H. Choi, M. G. Antoniou, M. Pelaez, A. A. de la Cruz, J. A. Shoemaker, D. D. Dionysiou, *Environ. Sci. Technol.* 41 (2007) 7530–7535. Copyright (2007) American Chemical Society).

the sol-gel synthesis. Such heterojunction photocatalysts seem to effectively transfer photo-excited electrons from the conduction band of anatase to that of rutile, favoring electron-hole separation and enhancing the visible light photocatalytic activity. [86,87]. Etacheri et al. have successfully developed nitrogen doped anatase-rutile heterojunctions which were found to be nine times more photocatalytically active at wavelengths higher than 450 nm (blue filter) in comparison with Evonik P25.

Most of the above methods have also been successfully applied for the doping of 1D titania nanostructures with nitrogen. In this way, N-doped anatase titania nanobelts were prepared via hydrothermal processing and subsequent heat treatment in NH_3 [88]. Similar post-treatment was employed for doping anodized titania nanotubes [89], while high energy ion implantation was found to be more efficient in introducing N atoms in the TiO_2 lattice [90]. Nitrogen localized states have also been introduced into highly ordered TiO_2 nanotubes via nitrogen plasma [91]. Visible light-active N- TiO_2 nanoarray films have also been prepared on sacrificial anodized alumina liquid phase deposition with urea mixed with $(\text{NH}_4)_2\text{TiF}_6$ aqueous solution [92]. Recently, surface N-doping on titania nanowires, their lateral dimensions reaching the atomic scale, was achieved by the introduction of amines during the condensation stage of the titania precursor [93]. Other approaches for preparing doped TiO_2 nanotubes

include employment of nitrogen sources in the electrolyte solutions of electrochemical anodization [94] or in the initial solution of hydrothermal growth [95,96].

Many results, up to now, describe nitrogen doping as substitutional element on the oxygen lattice sites or at interstitial lattice sites. The two sites can be in principle discriminated by X-ray photoelectron spectroscopy (XPS) relying on the distinct N1s binding energies at 396 and 400 eV, respectively [51,69,97–99]. XPS peak assignment for N-doped visible light activated titania is still under debate [57,100]. Many researchers reported that N1s peaks around 397 eV are representative of substitutional nitrogen [57,100,101] while peaks at binding energies >400 eV are assigned to NO (401 eV) or NO_2 (406 eV) indicating interstitial nitrogen [101]. Di Valentin et al. [57] employed density functional theory (DFT) to demonstrate interstitial nitrogen as π character NO within anatase TiO_2 . It was also found that there is no significant shift in the conduction or valence bands of the TiO_2 . The energy bonding states associated below the valence band and anti-bonding states present above the valence band. The anti-bonding π^* N–O orbitals between the TiO_2 valence band and conduction band is believed to facilitate visible light absorption by acting as a stepping stone for excited electrons between conduction and valence bands. N species different from the photoactive ones in N doped TiO_2 can interfere in spectroscopic measurements since they have peaks around 400 eV.

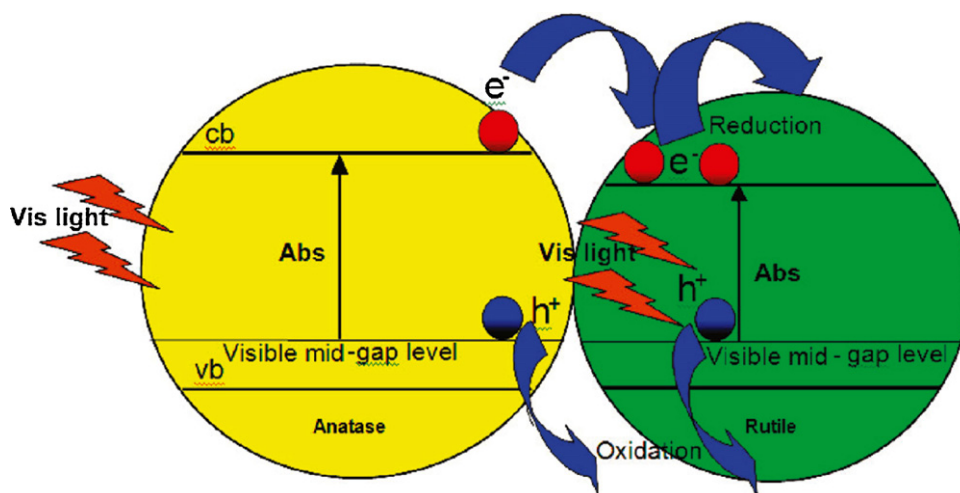


Fig. 4. Electron transfer mechanism in N-doped anatase rutile heterojunction. (Reprinted with permission from V. Etacheri, M. K. Seery, S. J. Hinder, S. C. Pillai, *Chem. Mater.* 22 (2010) 3843–3853. Copyright (2010) American Chemical Society).

However, XPS and electron paramagnetic resonance (EPR) evidence that N photoactive species corresponding to interstitial nitrogen with binding energy in the 400–401 eV region, prepared from glove discharge in molecular nitrogen in the presence of pure anatase, have been provided by Napoli et al. [102]. Moreover, Livraghi et al. showed that, by coupling XPS and solid state NMR, the 400 eV peak from ammonium ions reduces its intensity upon washing the solid [103]. Compared with the UV activity of undoped TiO₂, the visible light activity of N–TiO₂ is rather low. There is also some conflict in the literature concerning the preferred N sites, substitutional or interstitial, which induce the highest photocatalytic action [69,83,99,104]. Independently of the origin of visible light absorption in substitutional or interstitial nitrogen discrete energy states, the low photocatalytic efficiency is mainly attributed to the limited photo-excitation of electrons in such narrow states, the very low mobility of the corresponding photo-generated holes [105] and the concomitant increase of the recombination rate due to the creation of oxygen vacancies by doping [106].

2.1.2. Other non-metal doping (F, C, S)

Fluorine doping does not shift the TiO₂ band gap; however it improves the surface acidity and causes formation of reduced Ti³⁺ ions due to the charge compensation between F⁻ and Ti⁴⁺. Thus, charge separation is promoted and the efficiency of photoinduced processes is improved [107]. Insertion of fluorine into the TiO₂ crystal lattice has also been reported to elevate the anatase to rutile phase transformation temperature. Padmanabhan et al. successfully modified titanium isopropoxide with trifluoroacetic acid carrying out a sol–gel synthesis. The resulting material proved to be more photocatalytically active than Evonik P25 while also retaining anatase at temperatures of up to 900 °C [108].

Carbon, phosphorous and sulphur as dopants have also shown positive results for visible light activity in TiO₂ [48,49]. The non-metal dopants effectively narrow the band gap of TiO₂ (<3.2 eV) [50,109,110]. The change of lattice parameters, and the presence of trap states within the conduction and valence bands from electronic perturbations, gives rise to band gap narrowing [111]. Not only does this allow for visible light absorption but the presence of trap sites within the TiO₂ bands increases the lifetime of photo-generated charge carriers.

Successful insertion of sulfur into the TiO₂ lattice is far more difficult to achieve than nitrogen, due to its larger ionic radius. Insertion of cationic sulfur (S⁶⁺) is chemically favourable over the ionic form (S²⁻) lattice. Cationic (sulfur) and anionic (nitrogen) co-doped with TiO₂ has also been synthesised from a single source, ammonium sulfate, using a simple sol–gel technique [112]. Periyat et al. successfully developed S-doped TiO₂ through modification of titanium isopropoxide with sulphuric acid. They found that formation of titanyl oxysulfate results in the retention of anatase at increased temperatures (≥800 °C) and that the presence of sulfur causes increased visible light photocatalytic activity of the synthesised materials. [113]. Recently, visible light-activated sulfur doped TiO₂ films were successfully synthesized using a novel sol–gel method based on the self-assembly technique with a nonionic surfactant to control nanostructure and H₂SO₄ as an inorganic sulfur source [114]. Sulfur species distributed uniformly throughout the films were identified both as S²⁻ ions related to anionic substitutional doping of TiO₂ as well as S⁶⁺/S⁴⁺ cations, attributed mainly to the presence of surface sulfate groups. A strong EPR signal, whose intensity correlated with the sulfur content and most importantly was markedly enhanced under visible light irradiation, implied formation of localized energy states in the TiO₂ band gap due to anion doping and/or oxygen vacancies. Calcination at 350 °C for 2 h provided sulfur doped TiO₂ films with the highest sulfur content and BET surface area, small crystallite size, high porosity, and large pore volume together with very smooth and uniform surface.

The corresponding mesoporous S–TiO₂ film was the most effective photocatalyst for the degradation of microcystin-LR (MC-LR) under visible light irradiation.

2.1.3. Non-metal co-doping

N–F co-doped TiO₂ has been explored in visible light photocatalysis [115,116] due to the similar structural preferences of the two dopants. In addition, the combined structure retains the advantages of N-doping in high visible light response and the F-doping significant role in charge separation. Furthermore, synergetic effects of the co-doping have been found. In fact, surface fluorination inhibits phase transformation from anatase to rutile and removal of N-dopants during annealing [117]. In addition, it reduces the energy cost of doping and also the amount of oxygen defects in the lattice, as a consequence of the charge compensation between the nitrogen (*p*-dopant) and the fluorine (*n*-dopant) impurities [118]. These effects stabilize the composite system and effectively reduce the concomitant electron–hole recombination that hampers the photocatalytic performance of singly doped N–TiO₂.

The synergistic approach of the N–F doping has been further exploited employing a modified sol–gel technique based on a nitrogen precursor and a Zonyl FS-300 nonionic fluorosurfactant as both fluorine source and pore template material to tailor-design the structural properties of TiO₂ [119]. The obtained materials are active under visible light illumination and have been used for the photocatalytic degradation of a variety of pollutants in water. Very recently, these N–F doped titania materials were successfully immobilized on glass substrates employing the dip-coating method with subsequent drying under infrared lamp, followed by calcination at 400 °C. The nanostructured titania doped thin films preserve their visible light induced catalytic activity [120]. Furthermore, comparative EPR measurements between the co-doped and reference samples identified distinct N spin species in NF–TiO₂, with a high sensitivity to visible light irradiation. The abundance of these paramagnetic centers verifies the formation of localized intra-gap states in TiO₂ and implies synergistic effects between fluorine and nitrogen dopants [120].

Significant improvement of the visible-light photoactivity of N–F co-doped titania films has been observed by employing an inverse opal growth method, using a silica colloidal crystal as a template for liquid phase deposition of NF–TiO₂. In this way, hierarchical meso-macroporous structures are prepared which promote efficient and stable photocatalysis via tuned morphology and photon multiple scattering effects [121].

2.1.4. Oxygen rich TiO₂ modification

Following another approach, recently the visible light active photocatalytic properties have been achieved by the in situ generation of oxygen through the thermal decomposition of peroxo-titania complex [122]. Increased Ti–O–Ti bond strength and upward shifting of the valence band (VB) maximum were responsible for the visible light activity. The upward shifting of the VB maximum for oxygen rich titania is identified as another crucial reason responsible for efficient visible light absorption. Typical band gap structures of control and oxygen rich titania samples obtained are represented in Fig. 5.

2.2. Metal deposition

2.2.1. Noble metal and transition metal deposition

Modifications of TiO₂ with transition metals such as Cr, Co, V and Fe have extended the spectral response of TiO₂ well into the visible region also improving photocatalytic activity [107,123–128]. However, transition metals may also act as recombination sites for the photo induced charge carriers thus, lowering the quantum efficiency. Transition metals have also been found to cause

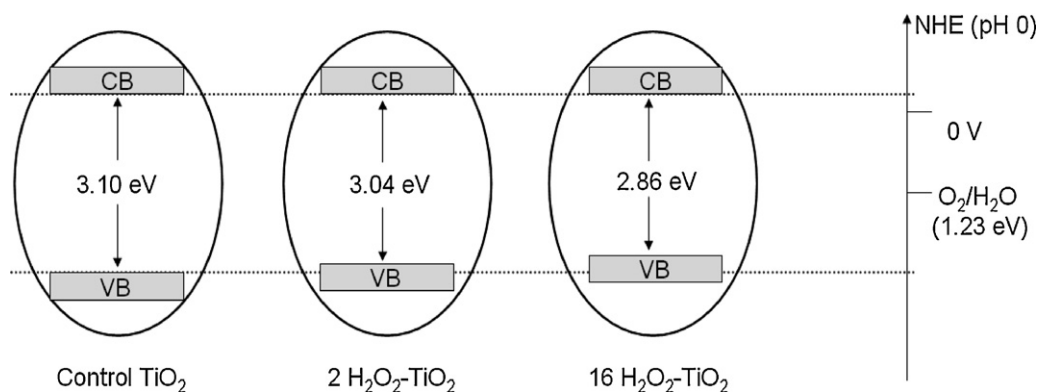


Fig. 5. Mechanism of band gap narrowing by oxygen excess. Number 2 and 16 in $\text{H}_2\text{O}_2\text{-TiO}_2$ was used to identified two different modified titania samples. (Reprinted with permission from V. Etacheri, M. K. Seery, S. J. Hinder, S. C. Pillai, *Adv. Funct. Mater.* 21 (2011) 3744–3752. Copyright (2011) Wiley VCH).

thermal instability to the anatase phase of TiO_2 [29]. Kang argues that despite the fact that a decrease in band gap energy has been achieved by many groups through metal doping, photocatalytic activity has not been remarkably enhanced because the metals introduced were not incorporated into the TiO_2 framework. In addition, metals remaining on the TiO_2 surface block reaction sites [129]. Morikawa et al. showed that doping TiO_2 with Cr was found to reduce photocatalytic activity but Cr and V ion implanted TiO_2 showed higher photocatalytic performances than bare TiO_2 did for the decomposition of NO under solar irradiation [130]. Another technique involves modifying TiO_2 with transition metals such as Fe, Cu, Co, Ni, Cr, V, Mn, Mo, Nb, W, Ru, Pt and Au [131–140]. The incorporation of transition metals in the titania crystal lattice may result in the formation of new energy levels between VB and CB, inducing a shift of light absorption towards the visible light region. Photocatalytic activity usually depends on the nature and the amount of doping agent. Possible limitations are photocorrosion and promoted charge recombination at metal sites [132].

Deposition of noble metals like Ag, Au, Pt and Pd on the surface of TiO_2 enhances the photocatalytic efficiency under visible light by acting as an electron trap, promoting interfacial charge transfer and therefore delaying recombination of the electron–hole pair [131,141–144]. Hwang et al. showed that platinum deposits on TiO_2 trap photo-generated electrons, and subsequently increase the photo-induced electron transfer rate at the interface. Seery et al. showed enhanced visible light photocatalysis with Ag modified TiO_2 [145]. While Gunawan et al. demonstrated the reversible photoswitching of nano silver on TiO_2 where reduced silver on a TiO_2 support exposed to visible light (>450 nm) resulted in excitation and reverse electron flow from silver to the TiO_2 support, oxidising silver ($\text{Ag}^0 \rightarrow \text{Ag}^+$) in the process [146]. The visible light responsiveness of TiO_2 was accredited to the surface plasmon resonance of silver nanoparticles (Fig. 6) [146,147].

2.3. Dye sensitization in photocatalysis

Dye photosensitization has been reported by different groups and to be one of the most effective ways to extend the photore-sponse of TiO_2 into the visible region [148–151]. Indeed these types of reactions are exploited in the well known dye sensitized solar cells [21]. The mechanism of the dye sensitized photo-degradation of pollutants is based on the absorption of visible light for exciting an electron from the highest occupied molecular orbital (HOMO) to the lowest unoccupied molecular orbital (LUMO) of a dye. The excited dye molecule subsequently transfers electrons into the conduction band of TiO_2 , while the dye itself is converted to its cationic radical. The TiO_2 acts only as a mediator for transferring electrons from the sensitizer to the substrate on the TiO_2 surface

as electron acceptors, and the valence band of TiO_2 remains unaffected. In this process, the LUMO of the dye molecules should be more negative than the conduction band of TiO_2 . The injected electrons hop over quickly to the surface of titania where they are scavenged by molecular oxygen to form superoxide radical $\text{O}_2^{\bullet-}$ and hydrogen peroxide radical $\bullet\text{OOH}$. These reactive species can also disproportionate to give hydroxyl radical [152–154]. In addition to the mentioned species, singlet oxygen may also be formed under certain experimental conditions. Oxygen has two singlet excited states above the triplet ground ones. Such relatively long live oxygen species may be produced by quenching of the excited state of the photosensitizer by oxygen. The subsequent radical chain reactions can lead to the degradation of the dye [154].

Knowledge of interfacial electron transfer between semiconductor and molecular adsorbates is of fundamental interest and essential for applications of these materials [155–158]. Ultrafast electron injection has been reported for many dye-sensitized TiO_2 systems. This injection depends on the nature of the sensitizer, the semiconductor, and their interaction. Asbury et al. observed very different electron injection times from femto to pico second by changing the semiconductor under the same conditions [156].

2.4. Coupled semiconductors

Many efforts have been made in the synthesis of different coupled semiconductors such as ZnO/TiO_2 [159], CdS/TiO_2 [160], and $\text{Bi}_2\text{S}_3/\text{TiO}_2$ [161]. The synthesized couples significantly enhance the photocatalytic efficiency by decreasing the recombination rate

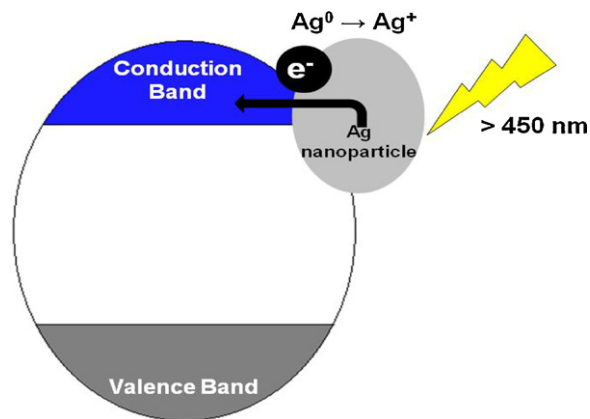


Fig. 6. Mechanism for light absorption of silver supported in TiO_2 . (Adapted with permission from N. T. Nolan, M. K. Seery, S. J. Hinder, L. F. Healy, S. C. Pillai *J. Phys. Chem. C* 114 (2010), 13026–13034. Copyright (2010) American Chemical Society).

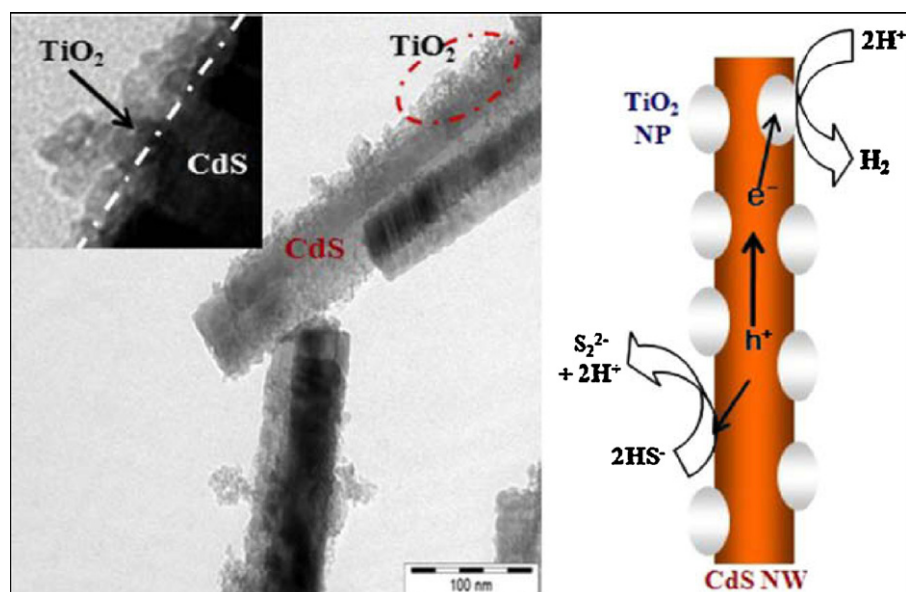


Fig. 7. TEM and mechanistic image of the interface between CdS nanowires and TiO₂ nanoparticles. TiO₂ provide sites for collecting the photoelectrons generated from CdS nanowires, enabling thereby an efficient electron–hole separation. (Reprinted with permission from S.J. Jum, G.K. Hyun, A.J. Upendra, W.J. Ji, S.L. Jae, *Int. J. Hydrogen Energy*, 33 (2008) 5975. Copyright (2008) Elsevier).

of the photogenerated electron–hole pairs and present potential applications in water splitting, organic decomposition, and photovoltaic devices [162–164]. These composites were also considered as promising materials to develop a high efficiency photocatalyst activated with visible light. They can also compensate the disadvantages of the individual components, and induce a synergistic effect such as an efficient charge separation and improvement of photostability [158,159]. Therefore, visible light-driven coupled photocatalysts that can decompose organic material are of great interest [163,166,167].

Analysis of the microstructure and phase composition of the coupled semiconductor of BiFeO₃/TiO₂ revealed that a core-shell structure was formed [168]. This couple resulted in extended photo-absorption bands into the visible which was dependent on the BiFeO₃ content. This couple was reported to be more effective for the photocatalytic degradation of congo red dye under visible light irradiation, as compared to pure BiFeO₃ and TiO₂ powders. Sensitizing TiO₂ nanotube arrays with ZnFe₂O₄ was found to enhance photoinduced charge separation and to extend the photoresponse from the UV to the visible region, too [169].

Up until now, the main efforts have been devoted to the synthesis of various core-shell nanocrystals. The prevalent view point is that it requires a lattice matching between shells and core materials to achieve a better passivation and minimize structural defects [164–173]. In addition, the coupling of a large band gap semiconductor with a smaller one, which can be activated with visible light, is of great interest for the degradation of organic pollutants using solar radiation. Blocking trap states by coating the particles with thin layers of a wide band gap material can lead to a drastic enhancement of the photostability [174–176]. For instance, CdS is a fascinating material with ideal band gap energy for solar and visible light applications (2.4 eV). However, CdS is prone to photo-anodic corrosion in aqueous environments. To overcome this stability problem and improve the photoactivity, CdS has been combined with a wide band gap semiconductor, such as ZnO and TiO₂ [163,177], and this coupling gives improved charge separation of photogenerated electrons and holes (see Fig. 7).

In addition to the flat band potential of the components, the photocatalytic performance of the coupled semiconductors is also related to the geometry of the particles, the contact surface between

particles, and the particle size [178,179]. These parameters strongly depend on the manner with which the couples are prepared. Various core/shell type nanocrystals have been extensively studied using different methods. Synthesis methods normally require high temperatures, long times, strict inert atmosphere protection and complex multistep reaction process.

By applying ultrasound under specific conditions, there is the possibility of synthesizing nano-composites in a short time, under mild conditions, in air, and without calcination [160]. For example, TiO₂-coated nanoparticles with a core-shell structure have been prepared with ultrasound treatment. The TiO₂ was found to be uniformly coated on the surface of CdS and this led to an enlargement of the nanoparticles. In the absence of ultrasound, the formation of large irregular aggregates was observed. The UV–vis absorbance spectra of the pure and composite semiconductors are shown in Fig. 8 [160]. The absorption band of CdS nanoparticles was found at around 450–470 nm in comparison with the bulk crystalline CdS which appeared at about 515 nm ($E_g = 2.4$ eV) [180]. In the case of

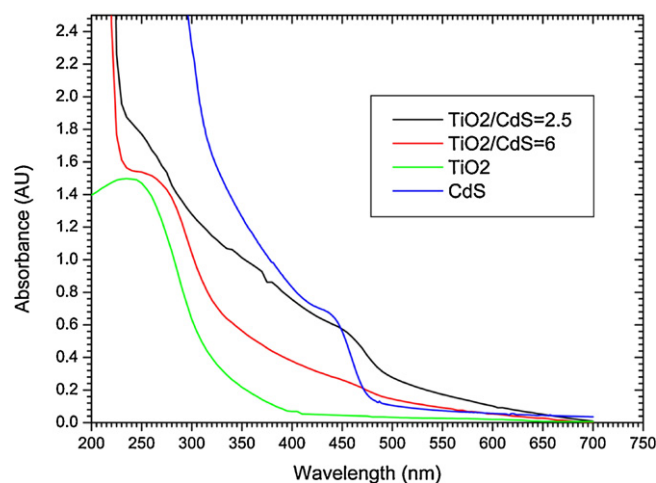


Fig. 8. The UV–vis absorbance spectra of pure and composite semiconductors. (Reprinted with permission from N. Ghows, M.H. Entezari, *Ultrason. Sonochem.*, 18 (2011) 629. Copyright (2008) Elsevier).

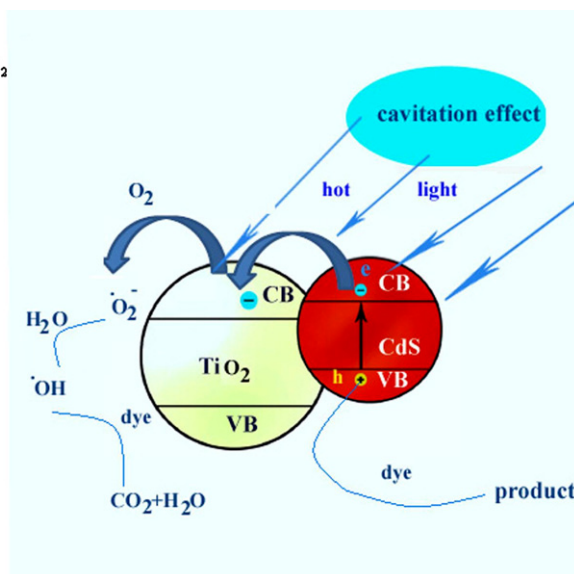










Fig. 9. Proposed mechanism that shows the interaction of one species from the core with one species from the shell for the removal of RB5 by nanocomposite Cds/TiO₂. (Reprinted with permission from Ref. [245]. Copyright (2011) Elsevier).

TiO₂, the onset absorption for nanoparticles prepared under ultrasound was about 360 nm, while for the bulk it was about 385 nm ($E_g = 3.2 \text{ eV}$) [181]. It is found that modification of TiO₂ with CdS particles extends the optical absorption spectrum into the visible region in comparison with that of pure TiO₂. Increasing the amount of TiO₂ led to a further red-shift of the absorption band in composite photocatalysts. The red shift of spectra are typical characteristics of core-shell nano-crystals, originating from the efficient diminishing of the surface defects of core nano-crystals after capping them with higher band gap shells [173]. This is in agreement with the previous report by Kisch et al. that the band gap of CdS employed in composite photocatalysts is shifted by an electronic semiconductor-support interaction [182,183].

The synthesized Cds/TiO₂ nano-composite system was applied for the removal of Reactive Black 5 in aqueous solution, under different conditions, and employing visible and solar light irradiation. The mechanism for the degradation that is proposed is based on the reactions in Fig. 9 [245]. In semiconductor core-shell structures electronic interactions that occur at the heterojunction can trap photo-generated electrons at the interface and improve the efficiency of the photocatalytic activity. The photo-generated electrons and holes induce redox reactions according to the relative potentials of the conduction and valence bands of the two semiconductors. Such core-shell nano-composites may bring new insights into the design of highly efficient photocatalysts and potential applications in technology.

2.5. Defect induced VLA photocatalysis

VLA titania can also be formed by introducing color centers inside the material [44,56]. This defect induced doping can be produced either by heat treatment of TiO₂ in vacuum or inert gas environments or by intercalation of small cations (H⁺, Li⁺, etc.) into the lattice. In some cases, O₂ is released from the material and Ti³⁺ centers are formed. Very recently, hydrogenation has been demonstrated as a very effective route to engineer the surface of anatase TiO₂ nanoparticles with an amorphous layer which, instead of inducing detrimental recombination effects, resulted in the marked extension of the optical absorption to the infrared range and remarkable enhancement of solar-driven photocatalytic activity [184].

3. Oxidation chemistry, the reactive oxygen species generated and their subsequent reaction pathways

3.1. Reactive oxygen species and reaction pathways in VLA TiO₂ photocatalysis

As a model, the reaction pathways of visible light-induced photocatalytic degradation of acid orange 7 (AO7) in the presence of TiO₂ has been investigated [185], monitoring the formation and the fate of intermediates and final products in solution and on the photocatalyst surface as a function of irradiation time. It was observed that the intensity of the chromophore band of AO7 reduced exponentially with time and disappeared after about 60 h. The intensities of the absorbance peaks related to the naphthalene and benzene rings in AO7 decreased with a slower rate compared to that of decolorization of the solution during the first 60 h. After complete decolorization, the absorbance due to the naphthalene and benzene rings remained constant. This observation confirmed that in the absence of colored compounds on the photocatalyst surface, visible light cannot effectively degrade fragments containing the benzene and naphthalene rings produced by the cleavage of the dye molecule. It should be noted that AO7 solution was stable under visible light without TiO₂, and that the TiO₂ suspension was unable to initiate the dye degradation in the dark. Both visible light and TiO₂ particles were indispensable for the degradation of AO7 in aqueous solution. During the irradiation of AO7-TiO₂ suspension with visible light different intermediates such as compounds containing a naphthalene ring, phthalic derivatives, aromatic acids, and aliphatic acids were identified. In addition, the evolution of inorganic ions such as sulfate, nitrate, nitrite, and ammonium ions were monitored during the irradiation by visible light.

By using appropriate quenchers, the formation of oxidative species such as singlet oxygen, superoxide, and hydroperoxide radicals and their role in the degradation of the dye molecules during illumination was studied [185]. It was observed that in the presence of 1,4-benzoquinone (BQ), which is a superoxide quencher and a good electron acceptor [123], both photodegradation and formation of hydrogen peroxide were completely suppressed. This indicates that the superoxide radical is an active oxidative intermediate. Addition of sodium azide, which is a singlet oxygen quencher [186] and may also interact with hydroxyl radical [187], initially did

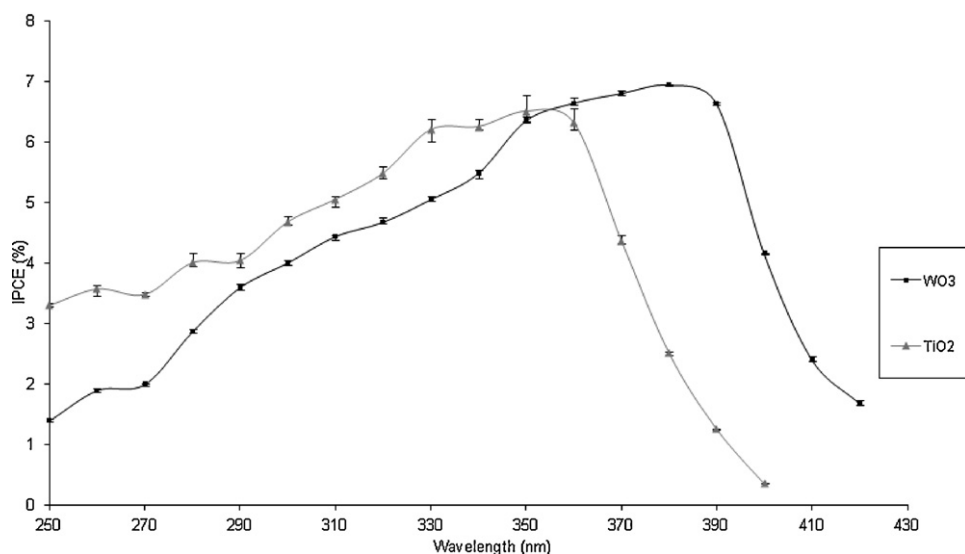


Fig. 10. %IPCE as a function of wavelength for the photooxidation of water on TiO₂ (red triangles) and WO₃ (blue squares) (Adapted with permission from J.W.J. Hamilton, J. A. Byrne, P. S. M. Dunlop, N. M. D. Brown, *International Journal of Photoenergy* (2008) Article ID 185479. Copyright (2008) Hindawi Publishing Corporation). (For interpretation of the references to color in this figure legend, the reader is referred to the web version of the article.)

not significantly affect the degradation of AO7 but the inhibition became important after 40 min, indicating the delayed formation of singlet oxygen and possibly hydroxyl radical species. Formation of hydrogen peroxide was also suppressed in the presence of this inhibitor. Similar results were obtained by addition of 1,4-diazabicyclo[2,2,2]-octane (DABCO) [188], which is also a singlet oxygen quencher. The important point of the work in [185] is that when complete decolorization of the solution was achieved, the formation of active oxidation species and hydrogen peroxide stopped, the oxidation reactions ceased and the concentrations of intermediates remained constant. This is because only in the presence of visible light absorbing compounds, the formation of oxidizing species was possible.

In a visible light/sensitizer/TiO₂ system, oxygen is indispensable in order to generate active oxygen radicals [189]. The role of dissolved oxygen and active species generated in the photocatalytic degradation of phenol was investigated by using a polymer sensitized TiO₂ under visible light [190]. The experimental results showed that the photocatalytic degradation of phenol was almost stopped under nitrogen atmosphere. Therefore, oxygen is very important in photocatalytic reactions induced by visible light and it acts as an efficient electron scavenger. In this system, the degradation of phenol gradually decreased by increasing sodium azide concentration. This indicated that singlet oxygen was generated under visible light irradiation. Singlet oxygen can degrade phenol directly to about 40% which is due to its high energy level (22.5 kcal mol⁻¹). In addition, singlet oxygen can be measured by phosphorescence in near IR as a direct method of detection. There is a range of different fluorescence or spin-trap probes for indirect measurements of singlet oxygen and/or superoxide. The spin-trap 2,2,6,6-tetramethyl-4-piperidone-*N*-oxide (TEMP) is generally used as a probe for singlet oxygen in EPR studies. The reactions of TEMP with singlet oxygen yields a stable radical adduct [191]. Another useful spin trap system is the 5,5 dimethylpyrrolineloxyde (DMPO) [192–194]. Monitoring intermediate 5,5 dimethylpyrrolineloxyde (DMPO)-OH• radicals formed in the suspension during illumination [190] is done by its characteristic 1:2:2:1 quartet EPR spectrum and provides evidence of hydroxyl radicals in the system. In addition, some alcohols are commonly used as diagnostic tools for hydroxyl radical mediated mechanisms [195,196]. The degradation of phenol by adding *i*-PrOH or MeOH was decreased

by about 60% which indicated that both of them seriously inhibited the photocatalytic degradation of phenol [190]. This confirmed that hydroxyl radicals were the predominant active species in this system, but did not probe the mechanism of hydroxyl radical formation.

3.2. Photoelectrochemical methods for determining visible light activity

If the photocatalytic material is immobilized onto an electrically conducting supporting substrate, one can use this electrode in a photoelectrochemical cell to measure properties including the band gap energy, flat band potential, dopant density, kinetics of hole and electron transfer, and the energies of dopant levels. If one examines the current-potential response under potentiometric control, for an n-type semiconductor e.g. TiO₂, in the dark no significant anodic (positive) current is observed because there are essentially no holes in the valence band. When irradiated with light equal to the band gap energy, electrons are promoted to the conduction band, leaving positive holes in the valence band, and an increase is observed in the anodic current at potentials more positive than the flat band potential E_{fb} . The difference between the current observed in the light and that in the dark is called the photocurrent (J_{ph}) and it is a measure of the hole-transfer rate at the SC-electrolyte interface. At the flat band potential, no net current is observed as all charge carriers recombine. For a p-type semiconductor, the situation is reversed and an increase in cathodic current is observed under band gap irradiation for potentials more negative than E_{fb} . If a monochromator is used along with a polychromatic source, e.g. xenon, to irradiate the electrode one can determine the spectral photocurrent response and the incident photon to current conversion efficiency (IPCE).

$$IPCE = \frac{J_{ph}}{I_0 F}$$

where J_{ph} is the photocurrent density (A cm⁻²), I_0 is the incident light flux (moles of photons s⁻¹ cm⁻²) and F is Faraday's constant (C mol⁻¹). For an n-type semiconductor, this is the quantum efficiency for hole-transfer to the electrolyte. The maximum wavelength at which photocurrent is observed will correlate to the band gap energy for the material. Therefore, the visible light activity can

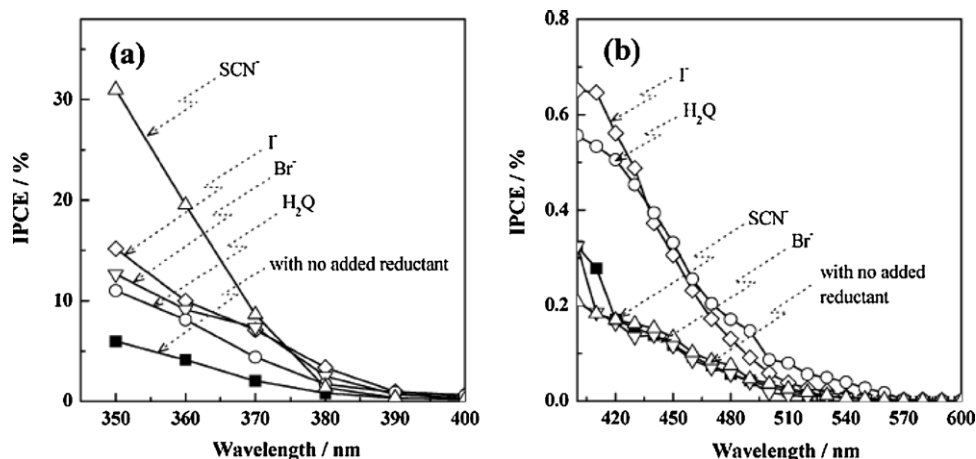



Fig. 11. Effect of the addition of 0.5 mM I⁻, H₂Q, SCN⁻, and Br⁻ on IPCE vs λ in the (a) UV- and (b) visible-light regions for N-doped TiO₂. The supporting electrolyte was 0.1 M HClO₄ and the electrode potential was 0.5 V vs Ag/AgCl (Reprinted with permission from R. Nakamura, T. Tanaka, Y. Nakato, *J. Phys. Chem. B* 108 (2004) 10617–10620. Copyright (2004) American Chemical Society).

be confirmed by simply using a light source with the desired emission spectrum to excite the electrode while monitoring the current as a function of applied potential. For example, Hamilton et al. [197] compared the spectral IPCE response between TiO₂ and WO₃ for the photooxidation of water (Fig. 10). WO₃ shows some activity in the visible with onset potential for anodic current positive relative to that observed for TiO₂.

In detailed work concerning the photoelectrochemical investigation of metal ion doped TiO₂, Hamilton et al. found that in all cases doping resulted in a decrease of the photocurrent response under solar simulated illumination [198]. However, a sub-band gap response (visible light activity) was observed for some samples. The sub-band gap photocurrent was potential dependent and could be correlated to oxygen vacancy states below the conduction band. The primary band-gap photocurrent response was decreased by the addition of metal ion dopants, which act as charge-carrier recombination centres, and the sub-band gap photocurrent was only a very small fraction of the band-gap photocurrent.

Nakamura et al. used photoelectrochemical methods to investigate the mechanism of visible light activity for N-doped TiO₂ powder prepared by both wet and dry methods [199]. The powder was immobilised on FTO glass by spin coating of a colloidal suspension (N-doped TiO₂/water/acetylacetone/HNO₃/Triton-X 100) followed by sintering at 400 °C. Photocurrents for undoped and N-doped TiO₂ film electrodes were measured as a function of wavelength, using a 350 W xenon lamp and a monochromator. The N-doped TiO₂ films gave a measurable IPCE% beginning around 525 nm (increasing with decreasing wavelength), whereas the undoped TiO₂ began to show a small IPCE% around 425 nm. To probe the mechanism further, they measured the IPCE% in the presence of different reductants (hole acceptors). Their basic theory was that those species with an oxidation potential more negative than the N-2p level can be oxidised by holes in this inter-band gap state (0.75 eV above the valence band) thus giving rise to an increase in the measured IPCE%, while those species with an oxidation potential more positive than the N-2p level cannot be oxidised by this state and therefore, no increase in IPCE% will be observed. They found that all reductants used caused an increase in the UV IPCE%, however, only I⁻ and hydroquinone gave an increase in the visible IPCE% (Fig. 11). Doping with N will give rise to a (occupied) mid-gap (N-2p) level slightly above the top of the (O-2p) valence band and visible-light illumination will generate holes in the mid-gap level, whereas UV illumination will generate holes in the (O-2p) valence band. The differences in the IPCE enhancement between UV and visible illumination can be attributed to differences in the

reactivity of these holes (Fig. 12). The measurement of the photocurrent should distinguish the above two oxidation processes because the photocurrent largely increases if a direct reaction with photogenerated holes occurs, whereas it there should be no difference observed if an indirect reaction via the intermediates of water photooxidation occurs. Nakamura et al. suggested that an increase in IPCE is not observed with the addition of SCN⁻ or Br⁻ because large reorganisation energies are required for the electron transfer reactions. Therefore, simply assuming the photocurrent (or reactivity) is only related to the redox potential of the reductant (hole acceptor) is not adequate for explaining visible light activity. Furthermore, photocurrent was observed under visible light irradiation for the photo-oxidation of water (no hole acceptor present) and the redox potential for the (·OH/H₂O) is more positive than the mid-gap N-2p level. Nakamura et al. reported that water photooxidation on n-TiO₂ (rutile) is not initiated by the oxidation of the surface OH group (Ti–OHs) with photogenerated holes (h⁺), but rather initiated by a nucleophilic attack of an H₂O molecule (Lewis base) to a surface hole (Lewis acid), accompanied by bond breaking.



The latter will not have any direct relation with the redox potential such as E_{eq} (·OH/H₂O) but will have a strong relation with the basicity of H₂O or the energy of an intermediate radical [Ti–O·

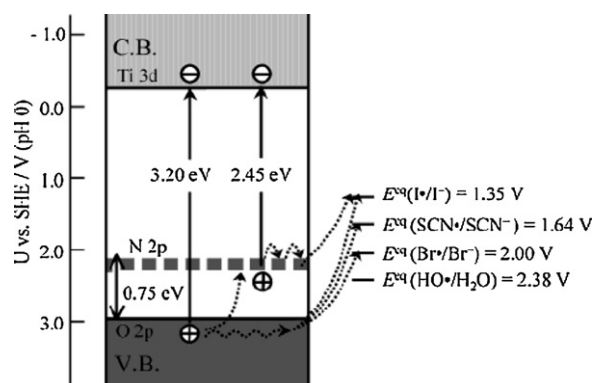


Fig. 12. Energy levels for N-doped TiO₂ (anatase) relative to reported equilibrium redox potentials for one-electron-transfer redox couples (Reprinted with permission from R. Nakamura, T. Tanaka, Y. Nakato, *J. Phys. Chem. B* 108 (2004) 10617–10620. Copyright (2004) American Chemical Society).

HO–Ti₅ that is roughly giving the activation energy for the reaction. They concluded that the observed photocurrent in the presence of reductants strongly depends on the reaction mechanism of oxidation and more knowledge is needed concerning the mechanism.

Beranek and Kisch reported the photoelectrochemical response of N-doped TiO₂ prepared by heating anodized titanium sheets and urea to 400 °C [200]. The resulting material consisted of a nitrogen-rich surface layer on the top of a nitrogen-poor core. The TiO₂–N thin films exhibit photocurrents in the visible up to 700 nm due to the presence of occupied nitrogen-centered surface states above the valence band edge (Fig. 13). The photocurrent transients significantly differed from those observed for undoped TiO₂ films and this could be explained by increased electron–hole recombination in TiO₂–N through these surface states. The addition of iodide partially suppressed the recombination due to hole scavenging. The flat band potential was determined by open circuit photopotential measurements and was anodically shifted by +0.2 V to –0.35 V (NHE) for TiO₂–N as compared to the undoped TiO₂.

Photoelectrochemical measurements can contribute significantly to the understanding of the mechanisms involved in the visible light activity of doped TiO₂ and other photocatalytic materials and can be combined with directly measuring the spectral dependence of the quantum efficiency for different pollutants [201]. More research is required to fully elucidate the mechanisms involved.

4. Environmental applications of VLA TiO₂

4.1. Water treatment and air purification with VLA photocatalysis

Conventional TiO₂ has been extensively studied for water treatment and air purification and it is well known to be an effective system to treat several hazardous compounds in contaminated water and air. Some focus is given nowadays to VLA TiO₂-based photocatalysis and its application towards remediation of regulated and emerging contaminants of concern.

Senthilnatan and Philip reported the degradation of lindane, an organochlorine pesticide, under visible light with different TiO₂ photocatalyst [202]. N-doped TiO₂, synthesized with different nitrogen containing organic compounds in a modified sol–gel method, showed better photocatalytic activity compared to other metal ions-doped TiO₂ and Evonik P25–TiO₂. Several phenoxyacid herbicides (i.e., mecopop, clopyralid) were photocatalytically transformed employing Fe-, N-doped anatase and rutile TiO₂ as well as undoped anatase and rutile TiO₂ under visible light irradiation [203]. Degradation rates of all pesticides employed were higher with N-doped anatase TiO₂ and the difference in photoreactivity was directly related to the molecular structure of the herbicide and its interaction with the radical species produced. 2,4-dichlorophenoxyacetic acid (2,4-D) is a widely used herbicide and found in surface and ground water from agricultural runoffs. Ag/TiO₂ photocatalyst, hydrothermally synthesized with template-assisted methods, effectively degraded 2,4-D under visible light [204]. Increasing Ag content diminished the photoreactivity of TiO₂ under the conditions tested. Also, increase in Ag concentration also increase the amount of brookite phase formed, affecting this the photoresponse of Ag/TiO₂.

The diverse group of substances, which are commonly detected at low concentration in the aqueous media and often are difficult to quantitatively remove from the water by conventional water treatment processes, can produce important damages in human health and in the aquatic environment, even at low concentrations. Some of these contaminants can have endocrine disruption effects in humans and aquatic organisms and the consequences of their exposure to organisms can go from developmental

problems to reproduction disorders. Wang and Lim developed several nitrogen and carbon doped TiO₂ via solvothermal method for the degradation of bisphenol-A under visible light-emitting diodes. The use of alternative visible light, such as light-emitting diodes, LEDs, provides several advantages, including energy efficiency, flexibility and extended lifetime [205]. All the synthesized CN–TiO₂ photocatalysts exhibited higher removal efficiencies for bisphenol-A than reference materials. In all cases, the highest extend of removal and mineralization was with emitting white light followed by blue, green and yellow light, in agreement with the adsorption edge of the doped TiO₂ materials. Neutral pH seems to be favorable for the degradation of this EDC in water. The presence of inorganic ions in the water matrix had different effects towards the degradation of bisphenol-A. Chloride, nitrate and sulfate ions partially inhibited the photocatalytic process while silica and bicarbonate scavenged to a greater extend the degradation of bisphenol-A under the conditions tested. In a related study, nitrogen-doped TiO₂ hollow spheres (NHS), prepared through ammonia treatment of monodispersed polystyrene spheres in a titania sol followed by heat treatment, were evaluated for the photocatalytic degradation of bisphenol-A under different light emitting LEDs [206]. NHS exhibited higher performance towards the degradation of bisphenol-A compared to undoped TiO₂ hollow spheres and TiO₂ powder. Nevertheless, the degree of degradation of bisphenol-A decreased from blue LED ($\lambda = 465$ nm) to yellow LED ($\lambda = 589$ nm) light, which is in agreement with Wang and Ling. Several intermediates detected were found to be reported previously with UV-irradiated TiO₂, thus following similar degradation pathways. Composite materials, such as nitrogen-doped TiO₂ supported on activated carbon (N–TiO₂/AC), have also been tested and proven to have a dual effect on the adsorption and photocatalytic degradation of bisphenol-A under solar light [207]. Even though the maximum adsorption capacity for bisphenol-A was reduced for N–TiO₂/AC compared to virgin AC at pH 3.0, higher photodegradation efficiencies were found for N–TiO₂/AC than with N–TiO₂ and undoped TiO₂ only at different excitation wavelengths.

Visible light active TiO₂ photocatalysts have also been employed for the photocatalytic degradation of cyanotoxins, in particular, the hepatotoxin microcystin-LR (MC-LR). MC-LR is a contaminant of emerging concern, highly toxic and frequently found cyanotoxin in surface waters. N–TiO₂ photocatalyst, described in section 2.1 as a one step process synthesis with DDAC as pore template and nitrogen dopant, efficiently degraded MC-LR under visible light. N–TiO₂ calcined at 350 °C showed the highest MC-LR degradation efficiency and an increase in calcination temperature resulted in a decrease of the photocatalytic activity of N–TiO₂ towards the removal of MC-LR. N–F co-doped TiO₂ nanoparticles synthesized from a modified sol–gel method were also applied for the degradation of MC-LR. Synergistic effects were observed with co-doped material, specifically in the photocatalytic improvement of MC-LR degradation at wavelengths >420 nm, compared to nitrogen and fluorine only doped TiO₂ and undoped TiO₂. A pH dependence was observed in the initial degradation rates of MC-LR where acidic conditions (pH 3.0) were favorable compare to higher pH values [119]. When immobilizing NF–TiO₂ on glass substrate, different fluorosurfactant molar ratios in the sol were tested and the efficiency of the synthesized photocatalytic films was evaluated for MC-LR removal. When increasing the fluorosurfactant ratio, higher MC-LR degradation rates were observed at pH 3.0 [120]. This is due to the effective doping of nitrogen and fluorine and the physicochemical improvements obtained with different surfactants loadings in the sol. Rhodium doped TiO₂, at high photocatalyst concentration, was shown to completely remove MC-LR under visible light conditions [208]. Much less active visible light photocatalyst for MC-LR degradation were TiO₂–Pt(IV) and carbon doped TiO₂ [208].

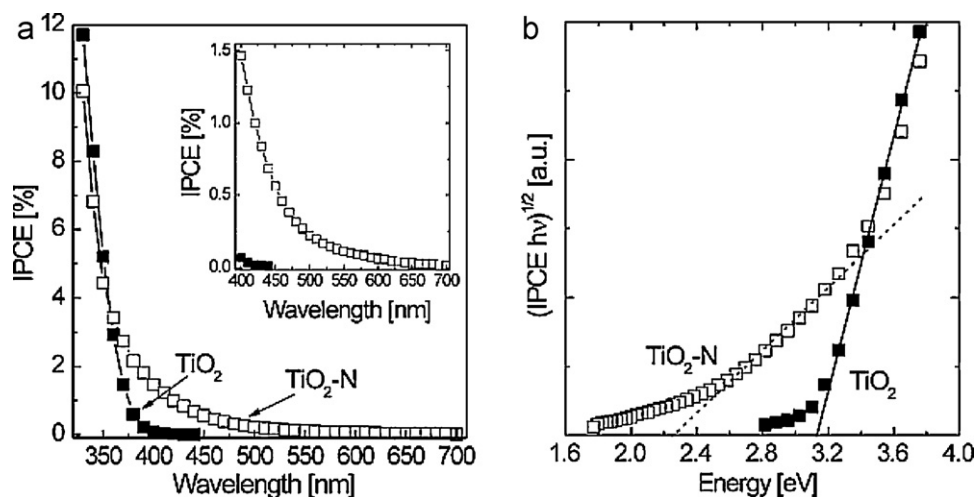


Fig. 13. IPCE spectra (a) and $(IPCE \text{ } hv)^{1/2}$ vs hv plots (b) for TiO_2 and $\text{TiO}_2\text{-N}$ recorded in LiClO_4 (0.1 M) + KI (0.1 M) (Reprinted with permission from R. Beranek and H. Kisch, *Electrochemistry Communications* 9 (2007) 761–766. Copyright (2007) Elsevier).


Volatile organic compounds (VOCs) are hazardous air pollutants that can be emitted into the atmosphere by a wide variety of industrial processes and cause adverse effects on the human nervous system, via breathing. A bifunctional photocatalyst, obtained from nitrogen-doped and platinum-modified TiO_2 ($\text{Pt}/\text{TiO}_{2-x}\text{N}_x$), was proven effective for the decomposition of benzene and other persistent VOCs under visible light irradiation in a $\text{H}_2\text{-O}_2$ atmosphere [209]. The doping of nitrogen and the incorporation of platinum played an important role in the enhancement of the visible light photocatalytic activity, mainly on the interfacial electron transfer at the surface of the photocatalyst. Ethyl benzene and *o,m,p*-xylenes were removed by employing N-TiO_2 at indoor air levels in an annular reactor even under typical humidified environments found indoors. Both low stream flow rates and low hydraulic diameter in the reactor are beneficial for higher degradation efficiencies. Composite N-TiO_2 /zeolite was investigated for the removal of toluene from waste gas. High porosity and effective visible light activation of the composite material gave a synergistic effect on the photocatalytic degradation of toluene compared to bare TiO_2 /zeolite [210]. This process was coupled to a biological treatment for further mineralization of toluene.

4.2. Water disinfection with VLA photocatalysis

Over the past ten years solar activated photocatalytic disinfection of water has received significant attention with research focus moving from laboratory studies to pilot experimentation [211]. VLA doped TiO_2 has also been investigated for a range of disinfection applications, including water purification. Twenty years after Matsunaga et al. published the first paper dealing with photocatalytic disinfection using a range of organisms and TiO_2 /Pt particles [212], Yu et al. described disinfection of the Gram positive bacterium *Micrococcus lylae* using sulfur-doped titanium dioxide exposed to 100W tungsten halogen lamp fitted with a glass filter to remove wavelengths less than 420 nm [213]. They reported 96.7% reduction in viable organisms following 1 h treatment in a slurry reactor containing 0.2 mg/mL S-doped- TiO_2 (1.96 at%), prepared via a copolymer sol-gel method. ESR measurements, using DMPO, confirmed the formation of hydroxyl radicals which were described as the reactive oxygen species responsible for the observed disinfection. Early work with N-doped TiO_2 , using *Escherichia coli* (*E. coli*) as the target organism, reported superior photocatalytic activity in comparison to Evonik P25 under solar light exposure [214]. Li et al. reported enhanced disinfection of

E. coli when VLA TiON was co-doped with carbon [215]. They attributed the additional biocidal effect to increased visible light absorption.

Mitoraj et al. describe VLA photocatalytic inactivation of a range of organisms, including Gram negative and Gram positive bacteria (*E. coli*, *Staphylococcus aureus* and *Enterococcus faecalis*) and fungi (*Candida albicans*, *Aspergillus niger*), using carbon-doped TiO_2 and TiO_2 modified with platinum(IV) chloride complexes in both suspension and immobilized reactor configurations [216]. The order of disinfection followed that commonly observed, whereby organisms with more significant cell wall structures proved more resistant to the biocidal species produced by photocatalysis: *E. coli* > *S. aureus* = *E. faecalis*. *C. albicans* and *A. niger* were much more resistant than the bacterial organisms examined. *E. coli* inactivation has also been reported using S-doped TiO_2 films, produced via atmospheric pressure chemical vapor deposition, upon excitation with fluorescent light sources commonly found in indoor healthcare environments [217]. A palladium-modified nitrogen-doped titanium oxide (TiON/PdO) photocatalytic fiber was used for the disinfection of MS2 phage by Li et al. [218]. Under dark conditions, significant virus adsorption was measured (95.4–96.7%) and upon subsequent illumination of the samples with visible light (>400 nm) for 1 h additional virus removal of 94.5–98.2% was achieved (the overall virus removal was 3.5-log from an initial concentration of $\sim 1 \times 10^8$ plaque forming units). EPR measurements were used to confirm the presence of $\bullet\text{OH}$ radicals. It was suggested that $\bullet\text{OH}$ radicals were formed via a reduction mechanism involving dissolved oxygen (Eqs. (3.1) and (3.2)).



Wu et al. produced titanium dioxide nanoparticles co-doped with N and Ag and investigated the efficiency of photocatalytic inactivation of *E. coli* under visible light irradiation ($\lambda > 400$ nm) [219]. A 5-log inactivation was observed after ca. 30 min irradiation, although disinfection was observed in the dark controls due to the biocidal properties of Ag ions. ESR studies demonstrated a significant increase in $\bullet\text{OH}$ production on the Ag, N-doped TiO_2 . Interactions between the ROS and *E. coli* resulted in physical damage to the outer membrane of the bacterial cell, structural changes within the plasma membrane were also observed. Similar structural and internal damage was suggested to be responsible for the

inactivation in *Pseudomonas aeruginosa* when exposed to sunlight in the presence of Zr doped TiO₂ [220].

Some of the most comprehensive studies on VLA TiO₂ disinfection have been undertaken by the Pulgarin group at EPFL, Switzerland. Commercial titania powders (Tayca TKP101, TKP102 and Evonik P25) were mechanically mixed with thiourea and urea to produce S-doped, N-doped and S, N co-doped VLA TiO₂ powders [221–224]. Various thermal treatments produced both interstitial and substitutional N-doping and cationic and anionic S-doped Tayca powders; thiourea treated P25 exhibited low level interstitial N-doping and anionic S-doping. Suspension reactor studies using *E. coli* showed that the doped Tayca materials were slightly less active than the non-doped powders during UV excitation, however, under visible light excitation (400–500 nm) the N, S co-doped powders outperformed the undoped powders, with those annealed at 400 °C resulting in 4-log *E. coli* inactivation following 75 min treatment [220]. The authors concluded that the nature of the doping (substitutional or interstitial N-doping and cationic or anionic S doping), surface hydroxylation and the particle size play important roles in the generation of biocidal ROS. In experiments with N, S co-doped Evonik P25, a 4-log *E. coli* inactivation was observed following 90 min exposure to visible light ($\lambda = 400\text{--}500\text{ nm}$) [221]. The authors proposed that upon UVA excitation the •OH radical is the most potent ROS, however; under visible excitation a range of ROS could be produced through reduction of molecular oxygen by conduction band electrons (superoxide radical anion, hydrogen peroxide and hydroxyl radicals), with singlet oxygen likely to be produced by the reaction of superoxide radical anion with localised N and S mid band-gap states [221]. Further mechanistic studies using N, S co-doped Tayca titania with phenol and dichloroacetate (DCA) as model probes, demonstrated complete *E. coli* disinfection but only partial phenol oxidation and no degradation of DCA under visible excitation [222]. Subsequent ESR experiments confirmed the production of both singlet oxygen and superoxide radical anion.

More recently, Rengifo-Herrera and Pulgarin investigated the use of N, S co-doped titania for disinfection under solar simulated exposure [225]. Using the photocatalyst in suspension, *E. coli* inactivation was observed with all doped and un-doped materials, however, the most efficient catalyst was undoped Evonik P25. Although the production of singlet oxygen and superoxide radical anion may contribute to the biocidal activity observed in N, S co-doped P25, under solar excitation the main species responsible for *E. coli* inactivation was the hydroxyl radical produced by the UV excitation of the parent material (Fig. 14). This finding clearly demonstrates that production of VLA photocatalytic materials for disinfection applications requires careful consideration of the ROS being generated and detailed experiments to show potential efficiency of new VLA materials.

5. Assessment of VLA photocatalyst materials

5.1. Standardization of test methods

Many researchers working in the field of photocatalysis are frustrated by the difficulty posed when attempting to compare results published by different laboratories. Long ago it was proposed that the extent of the difference in the photocatalytic experimental systems used could be identified if each group reported the initial rate of a standard test pollutant [226–229]. In the establishment of a standard test system, one of the most important factors is the determination of quantum yield or quantum efficiency. The overall quantum yield for a photoreaction (Φ_{overall}) is defined as follows [22],

$$\Phi_{\text{overall}} = \frac{\text{rate of reaction}}{\text{rate of absorption of radiation}} \quad (5.1)$$

In heterogeneous semiconductor photocatalysis, the Φ_{overall} is very difficult to measure due to the problems distinguishing between absorption, scattering and transmission of photons. A more practical term, the photonic efficiency (ξ), sometimes referred to as Φ_{apparent} , has been suggested:

$$\xi = \frac{\text{rate of reaction}}{\text{incident monochromatic light intensity}} \quad (5.2)$$

where the rate of absorption of radiation is simply replaced by the light intensity incident upon the reactor (or just inside the front window of the photoreactor). It is much simpler to determine the photonic efficiency than the true quantum yield. In addition the photonic efficiency is also a more practical quantity in terms of the process efficiency as the fraction of light scattered or reflected by semiconductor dispersion (or immobilized film) may be 13–76% of the incident light intensity. Thus the difference between Φ_{overall} and ξ may be significant. In research and practical applications, polychromatic light sources will be employed, and therefore one must replace ξ with the formal quantum efficiency (FQE);

$$\text{FQE} = \frac{\text{rate of reaction}}{\text{incident light intensity}} \quad (5.3)$$

For multi-electron photocatalytic degradation processes, the FQE will be much less than unity; unless a chain reaction is in operation. Therefore, it is most important that researchers specifically report their methods of quantum efficiency determination.

The solar spectrum contains only a small fraction of UV (4–5%) and this somewhat limits the application of wide band (UV absorbing) semiconductors, e.g. TiO₂, for solar energy driven water treatment. Even with good solar irradiance, the maximum solar efficiency achievable can only be 5%. The apparent quantum efficiency for the degradation of organic compounds in water is usually reported to be around 1% with UV irradiation, under optimum experimental conditions. Therefore, one can only reasonably expect an overall solar efficiency of around 0.05% for photocatalytic water treatment employing a UV band gap semiconductor.

A number of test systems have been proposed to assess the relative photocatalytic efficiency for the degradation of organic pollutants in water. For example, Mills et al. [229], suggested phenol/Evonik P25/O₂ or 4-chlorophenol/Evonik P25/O₂. In such a standard system, the experimental parameters would be defined, e.g. $[4\text{-chlorophenol}] = 10^{-3}\text{ mol dm}^{-3}$, $[\text{TiO}_2] = 500\text{ mg dm}^{-3}$, $[\text{O}_2] = 1.3 \times 10^{-3}\text{ mol dm}^{-3}$ ($P_{\text{O}_2} = 1\text{ atm}$), pH 2, $T = 30\text{ }^\circ\text{C}$. A comparison of the rate of the photocatalytic reaction under test with that obtained for the standard test system would provide some idea of the efficiency of the former process and allow some degree of comparison of results between groups. Other researchers [226–230] have suggested the use of relative photonic efficiencies (ξ_r), where both (initial) destruction rates of the tested pollutant and phenol as a model one with common molecular structure are obtained under exactly the same conditions.

$$\xi_r = \frac{\text{rate of disappearance of substrate}}{\text{rate of disappearance of phenol}} \quad (5.4)$$

However, Ryu and Choi reported that the photocatalytic activities can be represented in many different ways, and even the relative activity order among the tested photocatalysts depends on what substrate is used [231]. They tested eight samples of TiO₂ (suspension reactor) and each showed the best activity for at least one test-substrate. This highly substrate-specific activity of TiO₂ photocatalysts hinders the relative comparison of different catalyst materials. They proposed that a multi-activity assessment should be used for comparison of photocatalytic activity, i.e. four substrates should be examined: phenol, dichloroacetic acid (DCA), tetramethyl ammonium (TMA), and trichloroethylene (TCE) to take the substrate-specificity into account. They represent the aromatic,

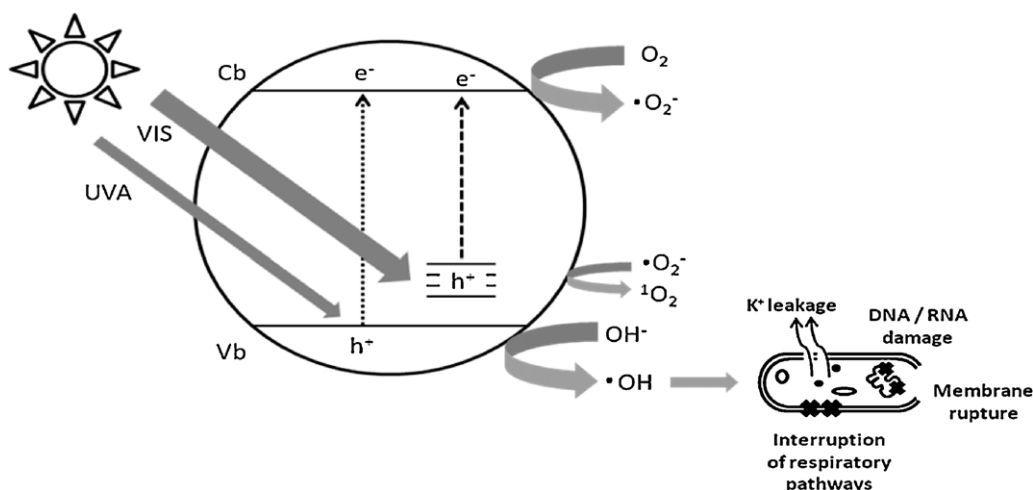


Fig. 14. Proposed bacterial disinfection mechanism during solar excitation of N, S co-doped TiO₂. (Adapted with permission from J. A. Rengifo-Herrera, C. Pulgarin, *Sol. Energy*, 84 (2010) 37–43. Copyright (2010) Elsevier).

anionic, cationic, and chlorohydrocarbon compounds, respectively, which are distinctly different in their molecular properties and structure.

The problems relating to the measurement of photocatalytic efficiency is further complicated when researchers attempt to compare the activities of 'visible light active' materials. Although visible light activity is in itself of fundamental interest, the test regime should consider the proposed application of the material. For example, if the application is purely a visible light driven process, e.g. self-cleaning surfaces for indoor applications, then a visible light source should be utilized for the test protocol. However, if the application is towards a solar driven process then simulated solar light or ideally real sun should be utilized for the test protocol. Many researchers investigate visible light activity by using a polychromatic source, e.g. xenon, and cutting out the UV component with a filter. That is important when determining the visible only activity; however, it is important the experiments are also conducted with light which corresponds to the solar spectrum, including ca. 5% UVA. When the UV activity of the material is good, this may outweigh any contribution from a relatively small visible light activity, hence the importance of photonic efficiency or FQE.

Doping of TiO₂ may give rise to a color change in the material as a result of the absorption of visible light however; an increase in visible absorption, in principle, does not guarantee visible light induced activity. Photocatalytic reactions proceed through redox reactions by photogenerated positive holes and photoexcited electrons. No activity may be observed if, for example, all of these species recombine. Various photocatalytic test systems with different model pollutants/substrates have been reported. Dyes are commonly used as model pollutants, partly because their concentration can be easily monitored using visible spectrophotometry; however, because the dyes also absorb light in the visible range, the influence of this photo-absorption by dyes should be excluded for evaluation of the real photocatalytic activity of materials. According to Herrmann [232], a real photocatalytic activity test can be erroneously claimed if a non-catalytic side-reaction or an artefact occurs. Dye decolorization tests can represent the most "subtle pseudo-photocatalytic" systems, hiding the actual non-catalytic nature of the reaction involved. An example of this dye sensitised phenomenon was reported with the apparent photocatalytic "disappearance" of indigo carmine dye [233]. The indigo carmine was totally destroyed by UV-irradiated titania; however, its colour also disappeared when using visible light but the corresponding total organic carbon (TOC) remained intact. The loss of colour actually corresponded to a limited transfer of electrons from the

photo-excited indigo (absorbing in the visible) to the TiO₂ conduction band. This 'dye sensitization' phenomenon is well known and exploited in the 'Gratzel' dye sensitized photovoltaic cell [21]. A dye which has been used widely as a test substrate for photocatalytic activity is methylene blue. Indeed the degradation of methylene blue is a recommended test for photocatalytic activity in the ISO/CD10678 [234]. Yan et al. reported on the use of methylene blue as a test substrate to evaluate the VLA for S-TiO₂ [235]. Two model photocatalysts were used, i.e. homemade S-TiO₂ and a commercial sample (Nippon Aerosil P-25) as a reference. Their results showed that a photo-induced reaction by methylene blue photo-absorption may produce results that could be mistaken to be evidence of visible-light photocatalytic activity. They suggested that dyes other than methylene blue should also be examined for their suitability as a probe molecule. Yan et al. used monochromatic light to determine the action spectrum enabling them to discriminate the origin of photoresponse by checking the wavelength dependence. However, most researchers simply use optical cut-off filters that transmit light above a certain wavelength. Yan et al. recommend the use of model organic substrates which do not absorb in the spectral region being used for excitation.

To complicate matters further, the photoreactor to be used in test reaction must be appropriate. It is good practice to compare any novel material with a relatively well established photocatalyst material, e.g. Evonik P25 [236]. The test system should utilize the catalyst in the same form - suspension or immobilized. Where suspension systems are employed, the catalyst must be well dispersed and an analysis of the particle size distribution should be undertaken. The optimum loading for each catalyst should also be determined. Where an immobilized catalyst system is employed, one must ensure that the reaction is not mass transfer limited otherwise the rate of degradation will simply be reflecting the mass transfer characteristics of the reactor. A high flow or a stirred tank system may be employed in an attempt to determine the intrinsic kinetics of the photocatalytic system [237].

Analysis of the literature concerning the development of visible light active photocatalytic materials for the destruction of organic pollutants in water shows that, while there has been enormous effort towards synthesis and characterisation of VLA materials, more attention has been paid to the photocatalysis test protocols. In the absence of a widely accepted standard test protocol, researchers should ensure the following, where possible: (1) the light source is appropriate with respect to the application and the emission spectrum is quantitatively determined, (2) more than one test substrate is used, e.g. multi-activity assessment proposed by Ryu and Choi

[230], and substrates absorbing light within the emission spectrum of the light source are avoided [234], (3) the reactor is well characterized, i.e. for suspension systems the particle size distribution is determined, (4) the photoreactor is appropriate and well characterized in terms of mass transfer; and (5) the photonic efficiencies or FQEs are reported along with the emission spectrum of the illumination source. Research and development for solar driven water treatment should utilize experiments under simulated or real solar irradiation, not just visible light sources.

5.2. Challenges in commercializing VLA photocatalysts

Some VLA TiO₂ photocatalytic products, like Kronos® VLP products, have already appeared in the market. Apart from the need for improvement on the photocatalytic efficiency, deactivation of TiO₂ photocatalysts over time has proven to be an inherent obstacle of the material that needs to be considered when commercializing VLA photocatalysts, in general [238]. Deactivation occurs when partially oxidized intermediates block the active catalytic sites on the photocatalyst [239]. Gas phase deactivation is more predominant than the aqueous phase, because in the aqueous phase, water assists in the removal of reaction intermediates from the photocatalyst surface [240]. The photocatalytic degradation of many organic compounds also generates unwanted by-products, which may be harmful to human health [22]. Certain elements and functional groups contained in organic molecules have been found to strongly hinder the photocatalytic ability of TiO₂ through deactivation. Peral and Ollis found that N or Si containing molecules may cause irreversible deactivation through the deposition of species that inhibit photoactive sites on the catalyst surface [241]. Carboxylic acids formed from alcohol degradation are also believed to strongly be adsorbed to the active sites of a catalyst and cause deactivation [22]. Strongly adsorbed intermediate species appear to commonly cause deactivation of a photocatalyst and it is certainly an area where further improvement is essential before TiO₂ can be considered a viable option for continuous photocatalytic applications.

Several researchers have been studying regeneration methods for the TiO₂ photocatalyst. Potential regeneration methods investigated include; thermal treatment (<400 °C) in air [242], sonication with water and methanol [243], irradiating the catalyst under UV light while passing humid air over the surface [244] and exposing the catalyst to air rich with H₂O₂, both with and without UV light [240].

6. Conclusions

In this review, titanium dioxide is introduced as a promising semiconductor photocatalyst due to its physical, structural and optical properties under UV light. In order to be photo-excited under visible light and aim at solar-driven TiO₂ photocatalysis, several synthesis methods have been successfully applied to achieve VLA TiO₂ photocatalysts. Non metal doping, in particular nitrogen doping, can be incorporated as substitutional or interstitial state in the TiO₂ lattice. Other non metals including carbon, fluorine and sulphur for doping and co-doping with nitrogen have been also investigated and shown visible light photo-induced activity. A variety of synthesis methods for noble metal and transition metal deposition, dye sensitization and coupling semiconductors have also extended the optical response of TiO₂ into the visible region. The reactive oxygen species generated with VLA TiO₂ under visible light indicate a different mechanism of photoactivation compared to UV light. The photocatalytic inactivation of a range of microorganisms has been explored using VLA TiO₂. High log reductions were observed for common microorganisms, like *E.coli*, with metal and non-metal doped TiO₂ under visible

and solar light. Moreover, the application of VLA TiO₂ for the removal of persistent and contaminants of emerging concern in water treatment and air purification has been effective compared to conventional TiO₂ under visible light. Therefore, these results are promising for further development of sustainable environmental remediation technologies, based on photocatalytic advanced oxidation processes driven by solar light as a renewable source of energy. Nevertheless, an effective assessment of VLA nanomaterials is needed to address several issues regarding test protocols, ensure true photocatalytic activity, and explore future commercialization of the material.

Acknowledgments

The authors wish to acknowledge financial support from NSF, Department of Employment and Learning Northern Ireland, Science Foundation Ireland (SFI) and NSF-CBET 1300 (Award 1033317) and the European Union's Seventh Framework Programme (FP7/2007–2013) under Grant agreement 227017 ("Clean Water" collaborative project). We also wish to thank Dr. John Colreavy, Director of CREST, DIT Dublin Ireland (and the vice-chair of the photocatalytic COST action-540), for supporting the research and reviewing the manuscript.

References

- [1] N.T. Nolan, M.K. Seery, S.C. Pillai, *Journal of Physical Chemistry C* 113 (2009) 16151–16157.
- [2] Y. Hu, H.-L. Tsai, C.-L. Huang, *European Ceramic Society* 23 (2003) 691–696.
- [3] D. Nicholls, *Complexes and First-Row Transition Elements*, MacMillan Education, Hong Kong, 1974.
- [4] Y. Shao, D. Tang, J. Sun, Y. Lee, W. Xiong, *China Particology* 2 (2004) 119–123.
- [5] O. Carp, C.L. Huisman, A. Reller, *Progress in Solid State Chemistry* 32 (2004) 33–177.
- [6] X. Chen, S.S. Mao, *Chemical Reviews* 107 (2007) 2891–2959.
- [7] X.-Q. Gong, A. Selloni, *Physical Review B: Condensed Matter* 76 (2007) 235307.
- [8] A. Wisitsoraat, A. Tuantranont, E. Comini, G. Sberveglieri, W. Wlodarski, *Thin Solid Films* 517 (2009) 2775–2780.
- [9] R. Asahi, Y. Taga, W. Mannstadt, A.J. Freeman, *Physical Review B: Condensed Matter* 61 (2000) 7459–7465.
- [10] A. Amtout, R. Leonelli, *Physical Review B: Condensed Matter* 51 (1995) 6842–6851.
- [11] M. Koelsch, S. Cassaignon, C.T. Thanh Minh, J.-F. Guillemoles, J.-P. Jolivet, *Thin Solid Films* 451 (2004) 86–92.
- [12] M.R. Hoffmann, S.T. Martin, W. Choi, D.W. Bahnemann, *Chemical Reviews* 95 (1995) 69–96.
- [13] M.A. Fox, M.T. Dulay, *Chemical Reviews* 93 (1993) 341–357.
- [14] Y. Wang, Y. Huang, W. Ho, L. Zhang, Z. Zou, S. Lee, *Journal of Hazardous Materials* 169 (2009) 77–87.
- [15] C. Su, C.-M. Tseng, L.-F. Chen, B.-H. You, B.-C. Hsu, S.-S. Chen, *Thin Solid Films* 498 (2006) 259–265.
- [16] A. Fujishima, K. Honda, *Nature* 238 (1972) 37–38.
- [17] S.N. Frank, A.J. Bard, *Journal of the American Chemical Society* 99 (1977) 303–304.
- [18] S.N. Frank, A.J. Bard, *Journal of Physical Chemistry* 81 (1977) 1484–1488.
- [19] J. Zhao, T. Wu, K. Wu, K. Oikawa, H. Hidaka, N. Serpone, *Environmental Science and Technology* 32 (1998) 2394–2400.
- [20] R. Wang, K. Hashimoto, A. Fujishima, M. Chikuni, E. Kojima, A. Kitamura, *Nature* 388 (1997) 431–432.
- [21] B. O'Regan, M. Gratzel, *Nature* 353 (1991) 737–739.
- [22] A. Mills, S. Le Hunte, *Journal of Photochemistry and Photobiology A* 108 (1997) 1–35.
- [23] P. Suppan, *Chemistry and Light*, Royal Society of Chemistry, Cambridge, 1994.
- [24] A. Testino, I.R. Bellobono, V. Buscaglia, C. Canevali, M. D'Arienzo, S. Polizzi, R. Scotti, F. Morazzoni, *Journal of the American Chemical Society* 129 (2007) 3564–3575.
- [25] T. Tachikawa, M. Fujitsuka, T. Majima, *Journal of Physical Chemistry C* 111 (2007) 5259–5275.
- [26] P.D. Cozzoli, R. Comparelli, E. Fanizza, M.L. Curri, A. Agostiano, *Materials Science and Engineering C* 23 (2003) 707–713.
- [27] A. Hoffman, E.R. Carraway, M. Hoffman, *Environmental Science and Technology* 28 (1994) 776–785.
- [28] C.A. Emilio, M.I. Litter, M. Kunst, M. Bouchard, C. Colbeau-Justin, *Langmuir* 22 (2006) 3606–3613.
- [29] W. Choi, A. Termin, M.R. Hoffmann, *Journal of Physical Chemistry B* 98 (1994) 13669–13679.
- [30] A. Scalfani, *Journal of Physical Chemistry* 100 (1996) 13655–13661.

- [31] J. Liqiang, Q. Yichun, W. Baiqi, L. Shudan, J. Baojiang, Y. Libin, F. Wei, F. Honggang, S. Jiazhong, *Solar Energy Materials & Solar Cells* 90 (2006) 1773–1787.
- [32] N. Serpone, *Journal of Photochemistry and Photobiology A* 104 (1997).
- [33] N. Serpone, D. Lawless, R. Khairutdinov, E. Pelizzetti, *Journal of Physical Chemistry* 99 (1995).
- [34] J. Soria, J.C. Conesa, V. Augugliaro, L. Palmisano, M. Schiavello, A. Sclafani, *Journal of Physical Chemistry* (1991) 95.
- [35] J.C. Yu, J.G. Yu, K.W. Ho, Z.T. Jiang, L.Z. Zhang, *Chemistry of Materials* (2002) 14.
- [36] Y.R. Do, K. Lee, K. Dwight, W. Wold, *Journal of Solid State Chemistry* (1994) 108.
- [37] J. Engweiler, J. Harf, A. Baiker, *Journal of Catalysis* (1996) 159.
- [38] K. Vinodgopal, P.V. Kamat, *Environmental Science and Technology* (1995) 29.
- [39] A.J. Maira, K.L. Yeung, C.Y. Lee, P.L. Yue, C.K. Chan, *Journal of Catalysis* (2000) 192.
- [40] Z.L. Xu, J. Shang, C.M. Liu, C. Kang, H.C. Guo, Y.G. Du, *Materials Science and Engineering B* (1999) 63.
- [41] Y. Li, D.-S. Hwang, N.H. Lee, S.-J. Kim, *Chemical Physics Letters* (2005) 404.
- [42] J. Yu, H. Yu, B. Cheng, M. Zhou, X. Zhao, *Journal of Molecular Catalysis A* 253 (2006).
- [43] M.D. Hernandez-Alonso, F. Fresno, S. Suarez, J.M. Coronado, *Energy & Environmental Science* 2 (2009) 1231–1257.
- [44] Y.-C. Nah, I. Paramasivam, P. Schmuki, *ChemPhysChem* 11 (2010) 2698.
- [45] V. Likodimos, T. Stergiopoulos, P. Falaras, J. Kunze, P. Schmuki, *Journal of Physical Chemistry C* 112 (2008) 12687–12696.
- [46] A.G. Kontos, A. Katsanaki, T. Maggos, V. Likodimos, A. Ghicov, D. Kim, J. Kunze, C. Vasilakos, P. Schmuki, P. Falaras, *Chemical Physics Letters* 490 (2010) 58.
- [47] A.G. Kontos, A.I. Kontos, D.S. Tsoukleris, V. Likodimos, J. Kunze, P. Schmuki, P. Falaras, *Nanotechnology* 20 (2009) 045603.
- [48] H. Irie, Y. Watanabe, K. Hashimoto, *Chemistry Letters* 32 (2003).
- [49] S. Sakthivel, H. Kisch, *Angewandte Chemie International Edition* 42 (2003).
- [50] T. Morikawa, R. Asahi, T. Ohwaki, K. Aoki, Y. Taga, *Japanese Journal of Applied Physics (JJAP)* 40 (2001).
- [51] A. Fujishima, X. Zhang, D.A. Tryk, *Surface Science Reports* 63 (2008) 515–582.
- [52] A.V. Emeline, V.N. Kuznetsov, V.K. Rybchuk, N. Serpone, *International Journal of Photoenergy* (2008) 258394.
- [53] S. Sato, *Chemical Physics Letters* 123 (1986) 126–128.
- [54] S. Sato, R. Nakamura, S. Abe, *Applied Catalysis A: General* 284 (2005) 131–137.
- [55] R. Asahi, T. Morikawa, T. Ohwaki, K. Aoki, Y. Taga, *Science* 293 (2001) 269–271.
- [56] N. Serpone, *Journal of Physical Chemistry B* 110 (2006) 24287–24293.
- [57] C. Di Valentin, E. Finazzi, G. Pacchioni, A. Selloni, S. Livraghi, M.C. Paganini, E. Giamello, *Chemical Physics* 339 (2007) 44–56.
- [58] S.U.M. Khan, M. Al-Shahry, W.B. Ingler, *Science* 297 (2002) 2243–2245.
- [59] Y. Izumi, T. Itoi, S. Peng, K. Oka, Y. Shibata, *Journal of Physical Chemistry C* 113 (2009) 6706–6718.
- [60] J. Zhang, Y. Wu, M. Xing, S.A.K. Leghari, S. Sajjad, *Energy & Environmental Science* 3 (2010) 715–726.
- [61] Y. Nakano, T. Morikawa, T. Ohwaki, Y. Yaga, *Applied Physics Letters* 86 (2005) 132104.
- [62] J.M. Mwabora, T. Lindgren, E. Avendano, T.F. Jaramillo, J. Lu, S.E. Lindquist, C.G. Granqvist, *Journal of Physical Chemistry B* 108 (2004) 20193–20198.
- [63] S.-H. Lee, E. Yamasue, H. Okumura, K.N. Ishihara, *Applied Catalysis A: General* 371 (2009) 179–190.
- [64] E. Martínez-Ferrero, Y. Sakatani, C. Boissière, D. Grosso, A. Fuentes, J. Fraxedas, C. Sanchez, *Advanced Functional Materials* 17 (2007) 3348–3354.
- [65] G. Abadias, F. Paumier, D. Eyidi, P. Guerin, T. Girardeau, *Surface and Interface Analysis* 42 (2010) 970–973.
- [66] J. Premkumar, *Chemistry of Materials* 16 (2006) 3980–3981.
- [67] Li Jinlong, M. Xinxin, S. Mingren, X. Li, S. Zhenlun, *Thin Solid Films* 519 (2010) 101–105.
- [68] A. Kafizas, C. Crick, I.P. Parkin, *Journal of Photochemistry and Photobiology A: Chemistry* 216 (2010) 156–166.
- [69] C.W.H. Dunnill, Z.A. Aiken, J. Pratten, M. Wilson, D.J. Morgan, I.P. Parkin, *Journal of Photochemistry and Photobiology A: Chemistry* 207 (2009) 244–253.
- [70] C. Sarantopoulos, A.N. Gleizes, F. Maury, *Thin Solid Films* 518 (2009) 1299–1303.
- [71] V. Pore, M. Heikkilä, M. Ritala, M. Leskelä, S. Arev, *Journal of Photochemistry and Photobiology A: Chemistry* 177 (2006) 68–75.
- [72] L. Zhao, Q. Jiang, J. Lian, *Applied Surface Science* 254 (2008) 4620–4625.
- [73] D. Mitoraj, H. Kisch, *Chemistry - A European Journal* 16 (2010) 261–269.
- [74] T.C. Jagadale, S.P. Takale, R.S. Sonawane, H.M. Joshi, S.I. Patil, B. Kale, S.B. Ogale, *Journal of Physical Chemistry C* 112 (2008) 14595–14602.
- [75] X. Qiu, Y. Zhao, C. Burda, *Advanced Materials* 19 (2007) 3995–3999.
- [76] T. Sano, N. Negishi, K. Koike, K. Takeuchi, S. Matsuzawa, *Journal of Materials Chemistry* 14 (2004) 380–384.
- [77] C. Belver, R. Bellod, A. Fuente, M. Fernandez-Garcia, *Applied Catalysis B: Environmental* 65 (2006) 301–308.
- [78] A.I. Kontos, A.G. Kontos, Y.S. Raptis, P. Falaras, *Physica Status Solidi (RRL)* 2 (2008) 83–85.
- [79] H. Choi, M.G. Antoniou, M. Pelaez, A.A. de la Cruz, J.A. Shoemaker, D.D. Dionysiou, *Environmental Science and Technology* 41 (2007) 7530–7535.
- [80] H. Choi, A.C. Sofranko, D.D. Dionysiou, *Advanced Functional Materials* 16 (2006) 1067–1074.
- [81] H. Choi, E. Stathatos, D.D. Dionysiou, *Applied Catalysis B* 63 (2006) 60–67.
- [82] X. Fang, Z. Zhang, Q. Chen, H. Ji, X. Gao, *Journal of Solid State Chemistry* 180 (2007) 1325–1332.
- [83] F.E. Oropeza, J. Harmer, R.G. Egdell, R.G. Palgrave, *Physical Chemistry Chemical Physics* 12 (2010) 960–969.
- [84] Y. Irokawa, T. Morikawa, K. Aoki, S. Kosaka, T. Ohwaki, Y. Taga, *Physical Chemistry Chemical Physics* 8 (2006) 1116–1121.
- [85] D.J.V. Pulsipher, I.T. Martin, E.R. Fisher, *Applied Materials & Interfaces* 2 (2010) 1743–1753.
- [86] V. Etacheri, M.K. Seery, S.J. Hinder, S.C. Pillai, *Chemistry of Materials* 22 (2010) 3843–3853.
- [87] Q. Li, J.K. Shang, *Journal of the American Ceramic Society* 91 (2008) 3167–3172.
- [88] J. Wang, De N. Tafen, J.P. Lewis, Z. Hong, A. Manivannan, M. Zhi, M. Li, N. Wu, *Journal of the American Chemical Society* 131 (2009) 12290–12297.
- [89] R.P. Vitiello, J.M. Macak, A. Ghicov, H. Tsuchiya, L.F.P. Dick, P. Schmuki, *Electrochemistry Communications* 8 (2006) 544–548.
- [90] A. Ghicov, J.-M. Macak, H. Tsuchiya, J. Kunze, V. Haeublein, L. Frey, P. Schmuki, *Nano Letters* 6 (2006) 1080–1082.
- [91] K.S. Han, J.W. Lee, Y.M. Kang, J.Y. Lee, J.K. Kang, *Small* 4 (2008) 1682–1686.
- [92] J. Wang, Z. Wang, H. Li, Y. Cui, Y. Du, *Journal of Alloys and Compounds* 494 (2010) 372–377.
- [93] C. Liu, H. Sun, S. Yang, *Chemistry - A European Journal* 16 (2010) 4381–4393.
- [94] K. Shankar, K.C. Tep, G.K. Mor, C.G. Grimes, *Journal of Physics D: Applied Physics* 39 (2006) 2361–2366.
- [95] D. Wu, M. Long, W. Caia, C. Chen, Y. Wu, *Journal of Alloys and Compounds* 502 (2010) 289–294.
- [96] G. Liu, L. Wang, C. Sun, Z. Chen, X. Yan, L. Cheng, H.-M. Cheng, G.Q. Lu, *Chemical Communications* (2009) 1383–1385.
- [97] X. Chen, Y. Lou, A.C.S. Samia, C. Burda, J.L. Cole, *Advanced Functional Materials* 15 (2005) 41–49.
- [98] M. Batzill, E.H. Morales, U. Diebold, *Physical Review Letters* 96 (2006) 026103–26104.
- [99] P. Romero-Gomez, V. Rico, A. Borrás, A. Barranco, J.P. Espinos, J. Cotrino, A.R. Gonzalez-Elipe, *Journal of Physical Chemistry C* 113 (2009) 13341–13351.
- [100] N.T. Nolan, D.W. Synnott, M.K. Seery, S.J. Hinder, A. Van Wassenhoven, S.C. Pillai, *Journal of Hazardous Materials* 211–212 (2012) 88–94.
- [101] J. Ananpattarachai, P. Kajitvichyanukul, S. Seraphin, *Journal of Hazardous Materials* 168 (2009) 253–261.
- [102] F. Napoli, M. Chiesa, S. Livraghi, E. Giamello, S. Agnoli, G. Granozzi, C. Di Valentin, G. Pacchioni, *Chemical Physics Letters* 477 (2009) 135–138.
- [103] S. Livraghi, M.R.C.E. Giamello, G. Magnacca, M.C. Paganini, G. Cappelletti, C.L. Bianchi, *Journal of Physical Chemistry C* 112 (2008) 17244–17252.
- [104] A. Braun, K.K. Akurati, G. Fortunato, F.A. Reifler, A. Ritter, A.S. Harvey, A. Vital, T. Graule, *Journal of Physical Chemistry C* 114 (2010) 516–519.
- [105] K. Hashimoto, H. Irie, A. Fujishima, *Japanese Journal of Applied Physics (JJAP)* 44 (2005) 8269–8285.
- [106] R. Katoh, A. Furube, K-i Yamanaka, T. Morikawa, *Journal of Physical Chemistry Letters* 1 (2010) 3261–3265.
- [107] A.M. Czoska, S. Livraghi, M. Chiesa, E. Giamello, S. Agnoli, G. Granozzi, E. Finazzi, C. Di Valentin, G. Pacchioni, *Journal of Physical Chemistry C* 112 (2008) 8951–8956.
- [108] S.C. Padmanabhan, S.C. Pillai, J. Colreavy, S. Balakrishnan, D.E. McCormack, T.S. Perova, Y. Gun'ko, S.J. Hinder, J.M. Kelly, *Chemistry of Materials* 19 (2007) 4474–4481.
- [109] K. Nagaveni, M.S. Hedge, N. Ravishanker, G.N. Subbanna, G. Madras, *Langmuir* 20 (2004) 2900–2907.
- [110] T. Umebayashi, T. Yamaki, H. Itoh, K. Asai, *Applied Physics Letters* 81 (2002) 454.
- [111] D.B. Hamal, K.J. Klabunde, *Journal of Colloid and Interface Science* 311 (2007) 514–522.
- [112] P. Periyat, D.E. McCormack, S.J. Hinder, S.C. Pillai, *Journal of Physical Chemistry C* 113 (2009) 3246–3253.
- [113] P. Periyat, S.C. Pillai, D.E. McCormack, J. Colreavy, S.J. Hinder, *Journal of Physical Chemistry C* 112 (2008) 7644–7652.
- [114] C. Han, M. Pelaez, V. Likodimos, A.G. Kontos, P. Falaras, K. O'Shea, D.D. Dionysiou, *Applied Catalysis B: Environmental* 107 (2011) 77–87.
- [115] Y. Xie, Y. Li, X. Zhao, *Journal of Molecular Catalysis A: Chemical* 277 (2007) 119–126.
- [116] S. Liu, J. Yu, W. Wang, *Physical Chemistry Chemical Physics* 12 (2010) 12308–12315.
- [117] G. Wu, J. Wen, S. Nigro, A. Chen, *Nanotechnology* 21 (2010) 085701.
- [118] C. Di Valentin, E. Finazzi, G. Pacchioni, A. Selloni, S. Livraghi, A.M. Czoska, M.C. Paganini, E. Giamello, *Chemistry of Materials* 20 (2008) 3706–3714.
- [119] M. Pelaez, A.A. de la Cruz, E. Stathatos, P. Falaras, D.D. Dionysiou, *Catalysis Today* 144 (2009) 19–25.
- [120] M. Pelaez, P. Falaras, V. Likodimos, A.G. Kontos, A.A. De la Cruz, K. O'Shea, D.D. Dionysiou, *Applied Catalysis B: Environmental* 99 (2010) 378–387.
- [121] J. Xu, B. Yang, M. Wu, Z. Fu, Y. Lv, Y. Zhao, *Journal of Physical Chemistry C* 114 (2010) 15251–15259.
- [122] V. Etacheri, M.K. Seery, S.J. Hinder, S.C. Pillai, *Advanced Functional Materials* 21 (2011) 3744–3752.
- [123] E. Borgarello, J. Kiwi, M. Gratzel, E. Pelizzetti, M. Visca, *Journal of the American Chemical Society* 104 (1982) 2996–3002.
- [124] M. Iwasaki, M. Hara, H. Kawada, H. Tada, S. Ito, *Journal of Colloid and Interface Science* 224 (2000) 202–204.
- [125] S. Klosek, D. Raftery, *Journal of Physical Chemistry B* 105 (2001) 2815–2819.

- [126] J. Zhu, F. Chen, J. Zhang, H. Chen, M. Anpo, *Journal of Photochemistry and Photobiology A* 180 (2006) 196–204.
- [127] N. Murakami, T. Chiyoya, T. Tsubota, T. Ohno, *Applied Catalysis A* 348 (2008) 148–152.
- [128] N. Murakami, A. Ono, M. Nakamura, T. Tsubota, T. Ohno, *Applied Catalysis B: Environmental* 97 (2010) 115–119.
- [129] M. Kang, *Materials Letters* 59 (2005) 3122–3127.
- [130] T. Morikawa, Y. Irokawa, T. Ohwaki, *Applied Catalysis A: General* 314 (2006) 123–127.
- [131] X.Z. Li, F.B. Li, *Environmental Science and Technology* 35 (2001) 2381–2387.
- [132] K. Demeestre, J. Dewulf, T. Ohno, P.H. Salgado, H.V. Langenhove, *Applied Catalysis B: Environmental* 61 (2005) 140–149.
- [133] D. Dvoranova, V. Brezova, M. Mazur, M.A. Malati, *Applied Catalysis B: Environmental* 37 (2002) 91–105.
- [134] A. Fuerte, M.D. Hernandez-Alonso, A.J. Maira, A. Martinez-Arias, M. Fernandez-Garcia, J.C. Conesa, J. Soria, *Chemical Communications* (2001) 2718–2719.
- [135] K. Iketani, R.-D. Sun, M. Toki, K. Hirota, O. Yamaguchi, *Materials Science and Engineering B* 108 (2004) 187–193.
- [136] F.B. Li, X.Z. Li, *Chemosphere* 48 (2002) 1103–1111.
- [137] T. Ohno, F. Tanigawa, K. Fujihara, S. Izumi, M. Matsumara, *Journal of Photochemistry and Photobiology A* 127 (1999) 107–110.
- [138] J.C.-S. Wu, C.-H. Chen, *Journal of Photochemistry and Photobiology A* 293 (2004) 509–515.
- [139] H. Yamashita, M. Harada, J. Misaka, M. Takeuchi, K. Ikeue, M. Anpo, *Journal of Photochemistry and Photobiology A* 148 (2002) 257–261.
- [140] H. Yamashita, M. Harada, J. Misaka, M. Takeuchi, B. Neppolian, M. Anpo, *Catalysis Today* 84 (2003) 191–196.
- [141] D. Behar, J. Rabani, *Journal of Physical Chemistry B* 110 (2006) 8750–8755.
- [142] Y. Zeng, W. Wu, S. Lee, J. Gao, *Catalysis Communications* 8 (6) (2007) 906–912.
- [143] W. Wang, J. Zhang, F. Chen, D. He, M. Anpo, *Journal of Colloid and Interface Science* 323 (2008) 182–186.
- [144] X. You, F. Chen, J. Zhang, M. Anpo, *Catalysis Letters* 102 (2005) 247–250.
- [145] M.K. Seery, R. George, P. Floris, S.C. Pillai, *Journal of Photochemistry and Photobiology A* 189 (2007) 258–263.
- [146] C. Gunawan, W.Y. Teoh, C.P. Marquis, J. Lifia, R. Amal, *Small* 5 (2009) 341–344.
- [147] N.T. Nolan, M.K. Seery, S.J. Hinder, L.F. Healy, S.C. Pillai, *Journal of Physical Chemistry C* 114 (2010) 13026–13034.
- [148] T. Wu, T. Lin, J. Zhao, H. Hidaka, N. Serpone, *Environmental Science and Technology* 33 (1999) 1379.
- [149] T. Wu, G. Liu, J. Zhao, H. Hidaka, N. Serpone, *Journal of Physical Chemistry B* 102 (1998) 5845.
- [150] Y. Cho, W. Choi, C.H. Lee, T. Hyeon, H.I. Lee, *Environmental Science and Technology* 35 (2001) 966.
- [151] Y. Xu, C.H. Langford, *Langmuir* 17 (2001) 897.
- [152] D. Chatterjee, S. Dasgupta, N.N. Rao, *Solar Energy Materials and Solar Cells* 90 (2006) 1013.
- [153] K. Vinodgopal, U. Stafford, K.A. Gray, P.V. Kamat, *Journal of Physical Chemistry* 98 (1994) 6797.
- [154] K. Vinodgopal, I. Bedja, P.V. Kamat, *Chemistry of Materials* 8 (1996) 2180.
- [155] A.J. Nozik, R. Memming, *Journal of Physical Chemistry* 100 (1996) 13061.
- [156] J.B. Asbury, E. Hao, Y. Wang, H.N. Ghosh, T. Lian, *Journal of Physical Chemistry B* 105 (2001) 4545.
- [157] P.V. Kamat, *Progress in Reaction Kinetics* 19 (1994) 277.
- [158] A. Hagfeldt, M. Gratzel, *Chemical Reviews* 95 (1995) 49.
- [159] G. Marci, V. Augugliaro, M.J. López-Muñoz, C. Martin, L. Palmisano, V. Rives, M. Schiavello, R.J.D. Tilley, A.M. Venezia, *Journal of Physical Chemistry B* 105 (2001) 1026.
- [160] N. Ghows, M.H. Entezari, *Ultrasonics Sonochemistry* 18 (2011) 629.
- [161] R. Brahim, Y. Bessekhouad, A. Bouguelia, M. Trari, *Catalysis Today* 122 (2007) 62.
- [162] P.V. Kamat, *Journal of Physical Chemistry C* 112 (2008) 18737.
- [163] S.J. Jum, G.K. Hyun, A.J. Upendra, W.J. Ji, S.L. Jae, *International Journal of Hydrogen Energy* 33 (2008) 5975.
- [164] K.S. Leshkies, R. Duvakar, J. Basu, E.E. Pommer, J.E. Boercker, C.B. Carter, U.R. Kortshagen, D.J. Norris, E.S. Aydil, *Nano Letters* 7 (2007) 1793.
- [165] J.S. Jang, S.M. Ji, S.W. Bae, H.C. Son, J.S. Lee, *Journal of Photochemistry and Photobiology A* 188 (2007) 112.
- [166] D. Robert, *Catalysis Today* 122 (2007) 20.
- [167] Y. Bessekhouad, D. Robert, J.-V. Weber, *Catalysis Today* 101 (2005) 315.
- [168] S. Li, Y.-H. Lin, B.-P. Zhang, J.-F. Li, C.-W. Nan, *Journal of Applied Physics (JJAP)* 105 (2009) 054310.
- [169] X.Y. Li, Y. Hou, Q.D. Zhao, G.H. Chen, *Langmuir* 27 (2011) 3113–3120.
- [170] I. Robel, V. Subramanian, M. Kuno, P.V. Kamat, *Journal of the American Chemical Society* 128 (2006) 2385.
- [171] A. Kongkanand, K. Tvrđy, K. Takechi, M. Kuno, P.V. Kamat, *Journal of the American Chemical Society* 130 (2008) 4007.
- [172] T. Trindade, P. O'Brien, N.L. Pickett, *Chemistry of Materials* 13 (2001) 3843.
- [173] C. Wang, H. Zhang, J. Zhang, M. Li, H. Sun, B. Yang, *Journal of Physical Chemistry C* 111 (2007) 2465.
- [174] K. Tvrđy, P.V. Kamat, *Journal of Physical Chemistry A* 113 (2009) 3765.
- [175] M. Shalom, S. Dor, S. Rühle, L. Grinis, A. Zaban, *Journal of Physical Chemistry C* 113 (2009) 3895.
- [176] R. Vogel, P. Hoyer, H. Weller, *Journal of Physical Chemistry* 98 (1994) 3183.
- [177] L. Spanhel, H. Weller, A. Henglein, *Journal of the American Chemical Society* 109 (1987) 6632.
- [178] Y. Bessekhouad, N. Chaoui, M. Trzpit, N. Ghazzal, D. Robert, J.V. Weber, *Journal of Photochemistry and Photobiology A: Chemistry* 183 (2006) 218.
- [179] N. Serpone, P. Marathamuthu, P. Pichat, E. Pelizzetti, H. Hidaka, *Journal of Photochemistry and Photobiology* 85 (1995) 247.
- [180] J. Wang, K.P. Loh, Y.L. Zhong, M. Lin, J. Ding, Y.L. Foo, *Chemistry of Materials* 19 (2007) 2566.
- [181] M. Ammar, F. Mazaleyrat, J.P. Bonnet, P. Audebert, A. Brosseau, G. Wang, Y. Champion, *Nanotechnology* 18 (2007) 285606.
- [182] S.S. Lee, K.W. Seo, S.H. Yoon, I.-W. Shim, K.-T. Byun, H.-Y. Kwak, *Bulletin of the Korean Chemical Society* 26 (2005) 1579.
- [183] K.-T. Byun, K.W. Seo, I.-W. Shim, H.-Y. Kwak, *Chemical Engineering Journal* 135 (2008) 168.
- [184] X. Chen, L. Liu, P.Y. Yu, S.S. Mao, *Science* 331 (2011) 746–750.
- [185] M. Styliadi, D.I. Kondarides, X.E. Verykios, *Applied Catalysis B: Environmental* 47 (2004) 189.
- [186] C. Schweitzer, R. Schmidt, *Chemical Reviews* 103 (2003) 1685.
- [187] E. Frati, A.-M. Khatib, P. Front, A. Panasyuk, F. Aprile, D.R. Mitrovic, *Free Radical Biology and Medicine* 22 (1997) 1139.
- [188] J. Bandara, J. Kiwi, *New Journal of Chemistry (NJC)* 23 (1999) 717.
- [189] D. Chatterjee, A. Mahata, *Catalysis Communications* 2 (2001) 1.
- [190] D. Zhang, R. Qiu, L. Song, B. Eric, Y. Mo, X. Huang, *Journal of Hazardous Materials* 163 (2009) 843.
- [191] Y. Lion, M. Delmelle, A. Van de Vorst, *Nature* 263 (1976) 442.
- [192] G.M. Liu, X.Z. Li, J.C. Zhao, S. Horikoshi, H. Hidaka, *Journal of Molecular Catalysis A: Chemical* 153 (2000) 221.
- [193] C.C. Chen, W.H. Ma, J.C. Zhao, *Journal of Physical Chemistry B* 106 (2002) 318.
- [194] W. Zhao, C.C. Chen, X.Z. Li, J.C. Zhao, *Journal of Physical Chemistry B* 106 (2002) 5022.
- [195] H. Park, W. Choi, *Journal of Physical Chemistry B* 108 (2004) 4086.
- [196] Y.X. Chen, S.Y. Yang, K. Wang, L.P. Lou, *Journal of Photochemistry and Photobiology A: Chemistry* 172 (2005) 47.
- [197] J.W.J. Hamilton, J.A. Byrne, P.S.M. Dunlop, N.M.D. Brown, *International Journal of Photoenergy* (2008) 1–5, Article ID 1648 185479.
- [198] J.W.J. Hamilton, J.A. Byrne, C. McCullagh, P.S.M. Dunlop, *International Journal of Photoenergy* (2008) 1–8, Article ID 1650 631597.
- [199] R. Nakamura, T. Tanaka, Y. Nakato, *Journal of Physical Chemistry B* 108 (2004) 10617–10620.
- [200] R. Beranek, H. Kisch, *Electrochemistry Communications* 9 (2007) 761–766.
- [201] A.V. Emeline, X. Zhang, M. Jin, T. Murakami, A. Fujishima, *Journal of Photochemistry and Photobiology A: Chemistry* 207 (2009) 13–19.
- [202] J. Senthilnatan, Ligy Philip, *Chemical Engineering Journal* 161 (2010) 83–92.
- [203] D.V. Sojic, V.N. Despotovic, N.D. Abazovic, M.I. Comor, B.F. Abramovic, *Journal of Hazardous Materials* 179 (2010) 49–56.
- [204] M.M. Mohamed, K.S. Khairou, *Microporous and Mesoporous Materials* 142 (2011) 130–138.
- [205] X. Wang, T.-T. Lim, *Applied Catalysis B: Environmental* 100 (2010) 355–364.
- [206] D.P. Subagio, M. Srinivasan, M. Lim, T.-T. Lim, *Applied Catalysis B: Environmental* 95 (2010) 414–422.
- [207] P.-S. Yap, T.-T. Lim, M. Lim, M. Srinivasan, *Catalysis Today* 151 (2010) 8–13.
- [208] D. Graham, H. Kisch, L.A. Lawton, P.K.J. Robertson, *Chemosphere* 78 (2010) 1182–1185.
- [209] D. Li, Z. Chen, Y. Chen, W. Li, H. Huang, Y. He, X. Fu, *Environmental Science and Technology* 42 (2008) 2130–2135.
- [210] Z. Wei, J. Sun, Z. Xie, M. Liang, S. Chen, *Journal of Hazardous Materials* 177 (2010) 814–821.
- [211] S. Malato, P. Fernandez-Ibanez, M.I. Maldonado, J. Blanco, W. Gernjak, *Catalysis Today* 147 (2009) 1–59.
- [212] T. Matsunaga, R. Tomoda, T. Nakajima, H. Wake, *FEMS Microbiology Letters* 29 (1985) 211–214.
- [213] J.C. Yu, W. Ho, J. Yu, H. Yip, P.K. Wong, J. Zhao, *Environmental Science and Technology* 39 (2005) 1175–1179.
- [214] Y. Liu, J. Li, X. Qiu, C. Burda, *Water Science and Technology* 54 (2006) 47–54.
- [215] Q. Li, R. Xie, Y.W. Li, E.A. Mintz, J.K. Shang, *Environmental Science and Technology* 41 (2007) 5050–5056.
- [216] D. Mitoraj, A. Janczyk, M. Strus, H. Kisch, G. Stochel, P.B. Heczko, W. Macyk, *Photochemistry & Photobiological Sciences* 6 (2007) 642–648.
- [217] C.W. Dunnill, Z.A. Aiken, A. Kafizas, J. Pratten, M. Wilson, D.J. Morgan, I.P. Parkin, *Journal of Materials Chemistry* 19 (2009) 8747–8754.
- [218] Q. Li, M.A. Page, B.J. Mariñas, J.K. Shang, *Environmental Science and Technology* 42 (2008) 6148–6153.
- [219] P. Wu, R. Xie, K. Imlay, J.K. Shang, *Environmental Science and Technology* 44 (2010) 6992–6997.
- [220] S. Swetha, S.M. Santhosh, R.G. Balakrishna, *Photochemistry and Photobiology* 86 (2010) 1127–1134.
- [221] J.A. Rengifo-Herrera, E. Mielczarski, J. Mielczarski, N.C. Castillo, J. Kiwi, C. Pulgarin, *Applied Catalysis B: Environmental* 84 (2008) 448–456.
- [222] J.A. Rengifo-Herrera, C. Pulgarin, *Journal of Photochemistry and Photobiology A: Chemistry* 205 (2009) 109–115.
- [223] J.A. Rengifo-Herrera, K. Pierzchala, A. Sienkiewicz, L. Forro, J. Kiwi, C. Pulgarin, *Applied Catalysis B: Environmental* 88 (2009) 398–406.
- [224] J.A. Rengifo-Herrera, K. Pierzchala, A. Sienkiewicz, L. Forr, J. Kiwi, J.E. Moser, C. Pulgarin, *Journal of Physical Chemistry C* 114 (2010) 2717–2723.
- [225] J.A. Rengifo-Herrera, C. Pulgarin, *Solar Energy* 84 (2010) 37–43.
- [226] N. Serpone, G. Sauve, R. Koch, H. Tahiri, P. Pichat, P. Piccinini, E. Pelizzetti, H. Hidaka, *Journal of Photochemistry and Photobiology A: Chemistry* 94 (1996) 191–203.

- [227] N. Serpone, R. Terzian, D. Lawless, P. Kennepohl, G. Sauve, *Journal of Photochemistry and Photobiology A: Chemistry* 73 (1993) 11–16.
- [228] R.W. Matthews, S.R. McEvoy, *Journal of Photochemistry and Photobiology A: Chemistry* 66 (1992) 355–366.
- [229] A. Mills, S. Morris, *Journal of Photochemistry and Photobiology A: Chemistry* 71 (1993) 75–83.
- [230] J.R. Bolton, R.G. Bircher, W. Tumas, C.A. Tolman, *Journal of Advanced Oxidation Technologies* 1 (1996) 13–17.
- [231] J. Ryu, W. Choi, *Environmental Science and Technology* 42 (2008) 294–300.
- [232] J.M. Herrmann, *Applied Catalysis B: Environmental* 99 (2010) 461–468.
- [233] M. Vautier, C. Guillard, J.M. Herrmann, *Journal of Catalysis* 201 (2001) 46–59.
- [234] International Standards Organization, Fine ceramics (advanced ceramics, advanced technical ceramics) – Determination of photocatalytic activity of surfaces in aqueous medium by degradation of methylene blue, ISO/CD10678.
- [235] X. Yan, T. Ohno, K. Nishijima, R. Abe, B. Ohtani, *Chemical Physics Letters* 429 (2006) 606–610.
- [236] P.S.M. Dunlop, A. Galdi, T.A. McMurray, J.W.J. Hamilton, L. Rizzo, J.A. Byrne, *Journal of Advanced Oxidation Technologies* 13 (2010) 99–106.
- [237] T.A. McMurray, J.A. Byrne, P.S.M. Dunlop, J.G.M. Winkelman, B.R. Eggins, B.R., E.T. McAdams, E.T., *Applied Catalysis A-General* 262 (2004) 105–110.
- [238] L. Zhang, J.C. Yu, *Catalysis Communications* 6 (2005) 684–687.
- [239] L.X. Cao, Z. Gao, S.L. Suib, T.N. Obee, S.O. Hay, J.D. Freihaut, *Journal of Catalysis* 196 (2000) 253–261.
- [240] E. Piera, J.A. Ayllon, X. Domenach, J. Peral, *Catalysis Today* 76 (2002) 259–270.
- [241] J. Peral, D.F. Ollis, *Photocatalytic Purification and Treatment of Water and Air*, Elsevier, New York, 1993.
- [242] U.R. Pillai, E. Sahle-Demessie, *Journal of Catalysis* 211 (2002) 434–444.
- [243] J. Shang, Y.F. Zhu, Y.G. Du, Z.L. Xu, *Journal of Solid State Chemistry* 166 (2002) 395–399.
- [244] M.M. Ameen, G.B. Raupp, *Journal of Catalysis* 184 (1999) 112–122.
- [245] N. Ghows, M.H. Entezari, *Journal of Hazardous Materials* 195 (2011) 132.